



Suitability for outdoor use of different combinations between polyurethane Decoral System® Powder coatings and heat transfer film Decoral System® must be assessed on www.decoral-system.com. (link: **TESTED FOR OUTDOOR USE**) or contacting our laboratory.

ilpero

L' idoneità all'impiego in esterno degli abbinamenti tra prodotti vernicianti poliuretanici Decoral System® e film sublimatici Decoral System® dovrà essere valutata sul sito internet www.decoral-system.com (alla voce **FINITURE ADATTE PER USO ESTERNO**) oppure contattando il nostro laboratorio.

MRK-005-0978



Powder Coating: DS 706 + Heat Transfer Film: 2203/03



Powder Coating: DS-0730S + Heat Transfer Film: 2203/03




Powder Coating: DS 725 + Heat Transfer Film: 2203/03



Powder Coating: DS-0716S + Heat Transfer Film: 2203/03



Powder Coating: DS 733 + Heat Transfer Film: 2203/03

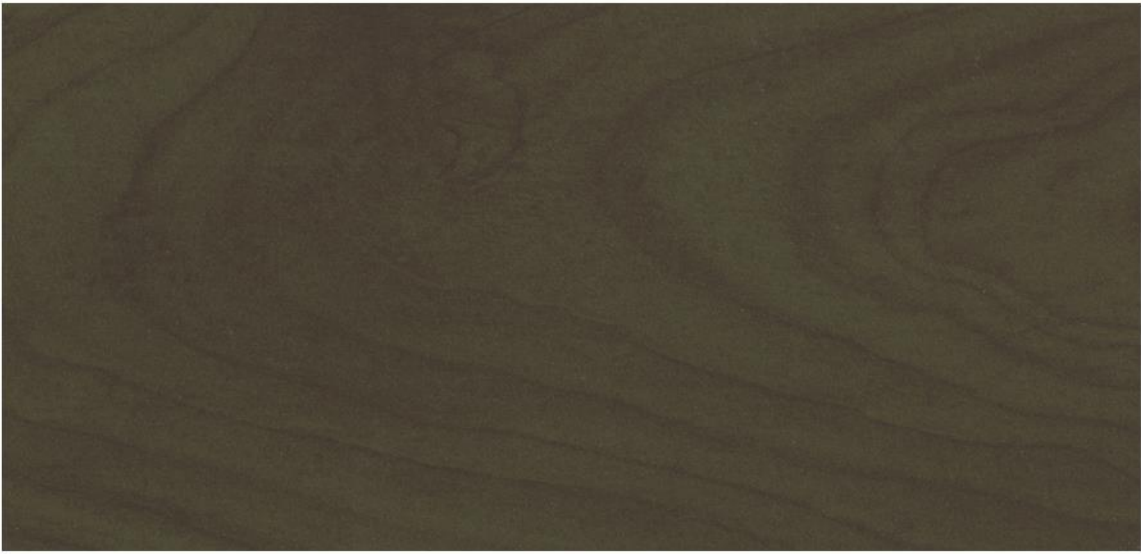

Powder Coating: DS-770 + Heat Transfer Film: 2203/03

Test Report: Accelerated Weathering Test		Decoral LAB Research and Development		60
Laboratory Test	No. 533	Device: QSun 3000	Total duration: 1117 h	
<p>Unexposed area (reference)</p> <p>Exposed area</p>				
LAB. ID NUMBER: 43978 POWDER COATING: DS 725 HEAT TRANSFER FILM: 2203/03 Colour Variation (ΔE): 1,1 residual gloss: 76%				
Technical Remarks Good residual gloss and low colour variation (ΔE), after 1117 hours.				Technical Opinion Suitable for OUTDOOR USE
<small>Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers. However, the resistance against accelerated weathering test is only one of the conditions necessary for the evaluation of the resistance of the finished product. For a final assessment see further analysis on natural exposure in Florida.</small>				
Mod_TR_01_rev03 Laboratory Decoral System Date: 11/04/2019 ID Report: TR-IA-60-2019				

Test Report: Accelerated Weathering Test		Decoral LAB Research and Development		56
Laboratory Test	No. 533	Device: QSun 3000	Total duration: 1117 h	
<p>Unexposed area (reference)</p> <p>Exposed area</p>				
LAB. ID NUMBER: 43973 POWDER COATING: DS 733 HEAT TRANSFER FILM: 2203/03 Colour Variation (ΔE): 1,57 residual gloss: 63%				
Technical Remarks Good residual gloss and low colour variation (ΔE), after 1117 hours.				Technical Opinion Suitable for OUTDOOR USE
<small>Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers. However, the resistance against accelerated weathering test is only one of the conditions necessary for the evaluation of the resistance of the finished product. For a final assessment see further analysis on natural exposure in Florida.</small>				
Mod_TR_01_rev03 Laboratory Decoral System Date: 11/04/2019 ID Report: TR-IA-56-2019				

Test Report: Accelerated Weathering Test		Decoral LAB Research and Development		55
Laboratory Test	No. 533	Device: QSun 3000	Total duration: 1117 h	
<p>Unexposed area (reference)</p> <p>Exposed area</p>				
LAB. ID NUMBER: 43970 POWDER COATING: DS-07165 HEAT TRANSFER FILM: 2203/03 Colour Variation (ΔE): 1,8 residual gloss: 98%				
Technical Remarks Excellent residual gloss and low colour variation (ΔE), after 1117 hours.				Technical Opinion Suitable for OUTDOOR USE
<small>Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers. However, the resistance against accelerated weathering test is only one of the conditions necessary for the evaluation of the resistance of the finished product. For a final assessment see further analysis on natural exposure in Florida.</small>				
Mod_TR_01_rev03 Laboratory Decoral System Date: 11/04/2019 ID Report: TR-IA-55-2019				

Test Report: Accelerated Weathering Test		Decoral LAB Research and Development		51
Laboratory Test	No. 533	Device: QSun 3000	Total duration: 1117 h	
<p>Unexposed area (reference)</p> <p>Exposed area</p>				
LAB. ID NUMBER: 43964 POWDER COATING: DS 706 HEAT TRANSFER FILM: 2203/03 Colour Variation (ΔE): 0,73 residual gloss: 72%				
Technical Remarks Good residual gloss and low colour variation (ΔE), after 1117 hours.				Technical Opinion Suitable for OUTDOOR USE
<small>Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers. However, the resistance against accelerated weathering test is only one of the conditions necessary for the evaluation of the resistance of the finished product. For a final assessment see further analysis on natural exposure in Florida.</small>				
Mod_TR_01_rev03 Laboratory Decoral System Date: 11/04/2019 ID Report: TR-IA-51-2019				

Test Report: Accelerated Weathering Test		Decoral LAB Research and Development		52
Laboratory Test	No. 533	Device: QSun 3000	Total duration: 1117 h	
<p>Unexposed area (reference)</p> <p>Exposed area</p>				
LAB. ID NUMBER: 43966 POWDER COATING: DS 770 HEAT TRANSFER FILM: 2203/03 Colour Variation (ΔE): 1,56 residual gloss: 85%				
Technical Remarks Excellent residual gloss and low colour variation (ΔE), after 1117 hours.				Technical Opinion Suitable for OUTDOOR USE
<small>Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers. However, the resistance against accelerated weathering test is only one of the conditions necessary for the evaluation of the resistance of the finished product. For a final assessment see further analysis on natural exposure in Florida.</small>				
Mod_TR_01_rev03 Laboratory Decoral System Date: 11/04/2019 ID Report: TR-IA-52-2019				

Test Report: Accelerated Weathering Test		Decoral LAB Research and Development		53
Laboratory Test	No. 533	Device: QSun 3000	Total duration: 1117 h	
<p>Unexposed area (reference)</p> <p>Exposed area</p>				
LAB. ID NUMBER: 43967 POWDER COATING: DS-07305 HEAT TRANSFER FILM: 2203/03 Colour Variation (ΔE): 1,26 residual gloss: 100%				
Technical Remarks Excellent residual gloss and low colour variation (ΔE), after 1117 hours.				Technical Opinion Suitable for OUTDOOR USE
<small>Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers. However, the resistance against accelerated weathering test is only one of the conditions necessary for the evaluation of the resistance of the finished product. For a final assessment see further analysis on natural exposure in Florida.</small>				
Mod_TR_01_rev03 Laboratory Decoral System Date: 11/04/2019 ID Report: TR-IA-53-2019				