



**Test Reports**

**FIVE YEARS**  
**UNDER SOUTH FLORIDA SUN**

**QUALITYDECORAL® PLATINUM certified finishings**

POWDER COATING	FILM HYPERDURABLE	ID REPORT
17C-906-A001	81001/09 L4	TR-QDP-51-2020
17C-921-A001	81304/01 L4	TR-QDP-35-2020
17C-908-A001	81304/02 L8	TR-QDP-26-2020
17C-906-A001	81401/01 L4	TR-QDP-23-2020
17C-921-A001	81403/01 L4	TR-QDP-50-2020
17C-921-A001	81412/03 L4	TR-QDP-37-2020
17C-942-A001	81412/03 L4	TR-QDP-41-2020
17C-921-A001	81441/01 L4	TR-QDP-46-2020
17C-902-A001	81501/02 L4	TR-QDP-49-2020
17C-902-A001	81502/02 L4	TR-QDP-18-2020
17C-902-A001	81601/06 L4	TR-QDP-47-2020
17C-930-A001	82102/01 L4	TR-QDP-44-2020
17C-902-A001	82103/01 L4	TR-QDP-45-2020
17C-930-A001	82103/01 L4	TR-QDP-48-2020
17C-902-A001	82118/01 L4	TR-QDP-30-2020
17C-945-A001	82305/16 L8	TR-QDP-12-2020
17G-945-A005	82305/16 L8	TR-QDP-19-2020
17C-921-A001	82308/21 L4	TR-QDP-36-2020
17C-902-A001	82501/05 L4	TR-QDP-29-2020
17C-908-A001	82501/15 L8	TR-QDP-32-2020
17G-908-A005	82501/15 L8	TR-QDP-05-2020
17C-902-A001	82502/01 L4	TR-QDP-43-2020
17C-925-A001	82503/07 L4	TR-QDP-52-2020
17C-902-A001	82503/12 L4	TR-QDP-31-2020
17C-921-A001	82505/02 L4	TR-QDP-42-2020
17C-908-A001	82505/10 L8	TR-QDP-27-2020
17G-908-A005	82505/10 L8	TR-QDP-04-2020
17C-902-A001	82506/02 L4	TR-QDP-39-2020
17C-945-A001	82513/04 L8	TR-QDP-22-2020
17G-945-A005	82513/04 L8	TR-QDP-14-2020
17C-942-A001	82531/01 L4	TR-QDP-33-2020
17C-921-A001	82531/02 L4	TR-QDP-38-2020
17C-908-A001	82531/03 L8	TR-QDP-21-2020
17C-945-A001	82531/03 L8	TR-QDP-07-2020
17G-908-A005	82531/03 L8	TR-QDP-09-2020
17G-945-A005	82531/03 L8	TR-QDP-01-2020
17C-942-A001	82602/02 L4	TR-QDP-40-2020
17C-902-A001	82602/04 L8	TR-QDP-20-2020
17C-945-A001	82602/04 L8	TR-QDP-17-2020
17G-945-A005	82602/04 L8	TR-QDP-13-2020
MIRROR-058S25	85001/01 L8	TR-QDP-03-2020
17G-908-A005	85001/02 L8	TR-QDP-06-2020
MIRROR-058S25	85001/02 L8	TR-QDP-02-2020
MIRROR-058S25	85001/02 L8	TR-QDP-08-2020
MIRROR-058S25	85014/01 L4	TR-QDP-28-2020
MIRROR-058S25	85014/03 L4	TR-QDP-15-2020
MirrorL-183S25	86047/04 L4	TR-QDP-34-2020
MIRROR-113S25	86047/04 L4	TR-QDP-25-2020
MIRROR-113S25	86047/15 L4	TR-QDP-16-2020
MirrorL-183S25	86047/15 L4	TR-QDP-24-2020
MIRROR-113S25	86053/01 L4	TR-QDP-10-2020
MirrorL-183S25	86053/01 L4	TR-QDP-11-2020



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47422  
POWDER COATING: 17G-945-A005  
HEAT TRANSFER FILM: 82531/03 L8  
colour variation ( $\Delta E$ ): 1,26  
residual gloss: 58%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.




Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**

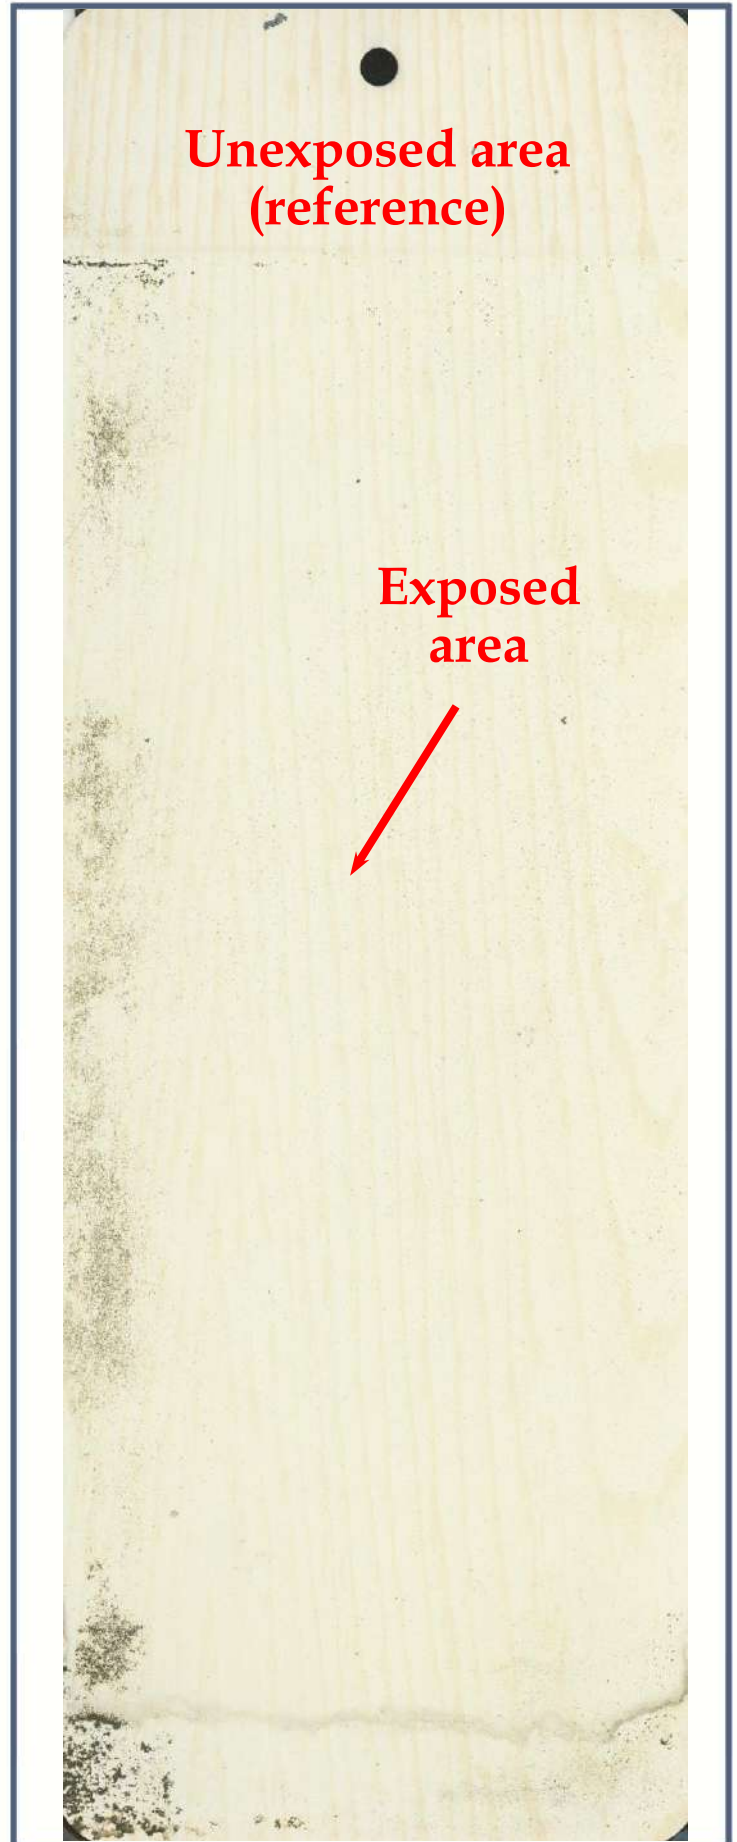



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47423  
POWDER COATING: Mirror-058S25  
HEAT TRANSFER FILM: 85001/02 L8  
colour variation ( $\Delta E$ ): 1,40  
residual gloss: 44%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a low residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47424  
POWDER COATING: Mirror-058S25  
HEAT TRANSFER FILM: 85001/01 L8  
colour variation ( $\Delta E$ ): 1,41  
residual gloss: 45%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a low residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

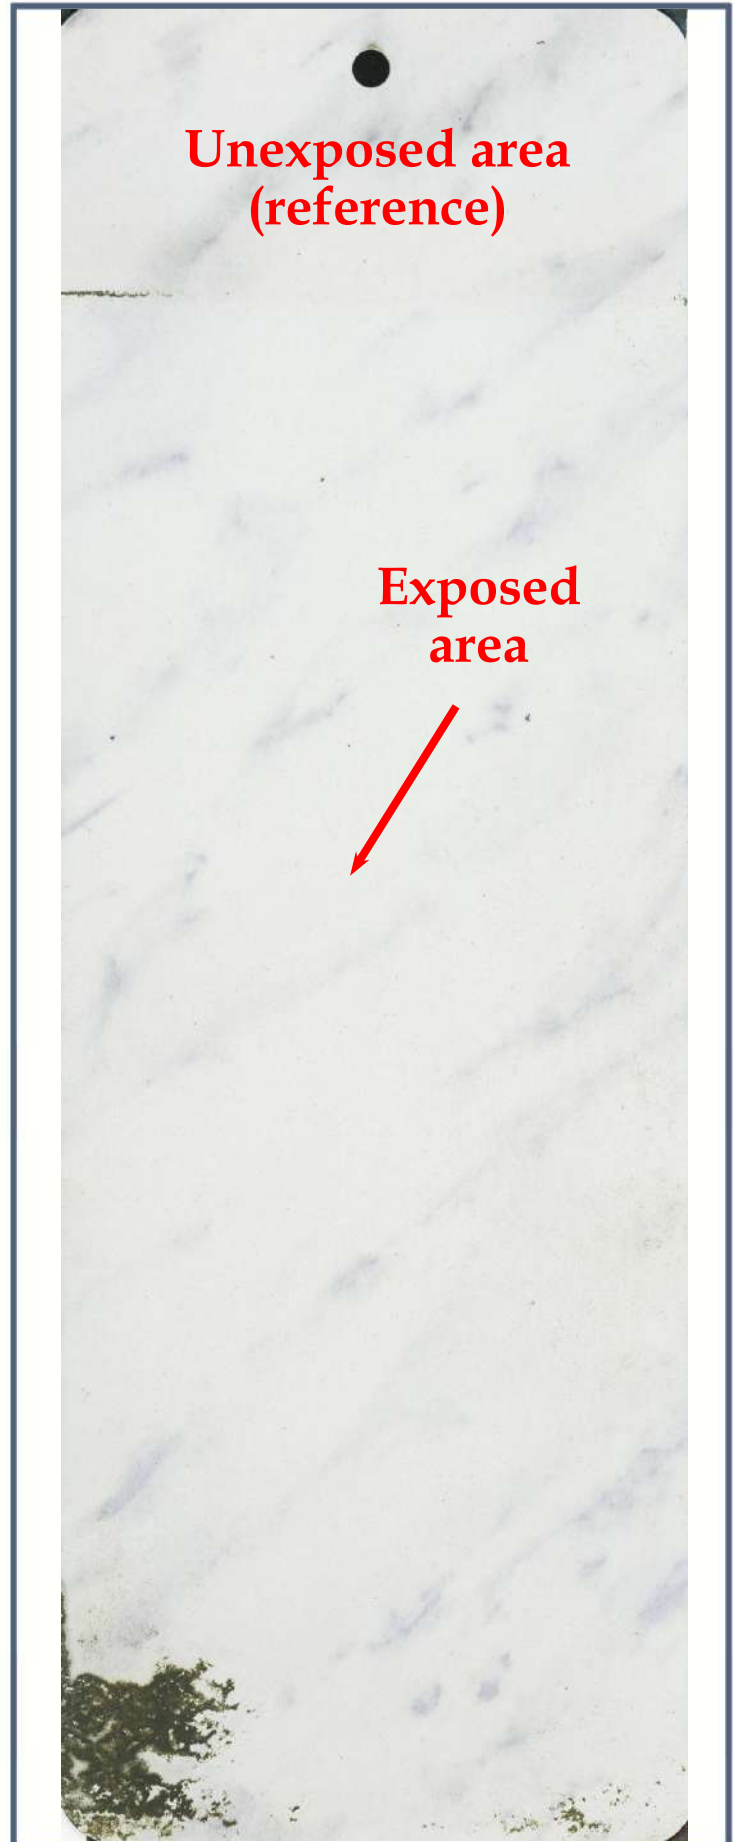



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47425  
POWDER COATING: 17G-908-A005  
HEAT TRANSFER FILM: 82505/10 L8  
colour variation ( $\Delta E$ ): **1,47**  
residual gloss: **44%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a low residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

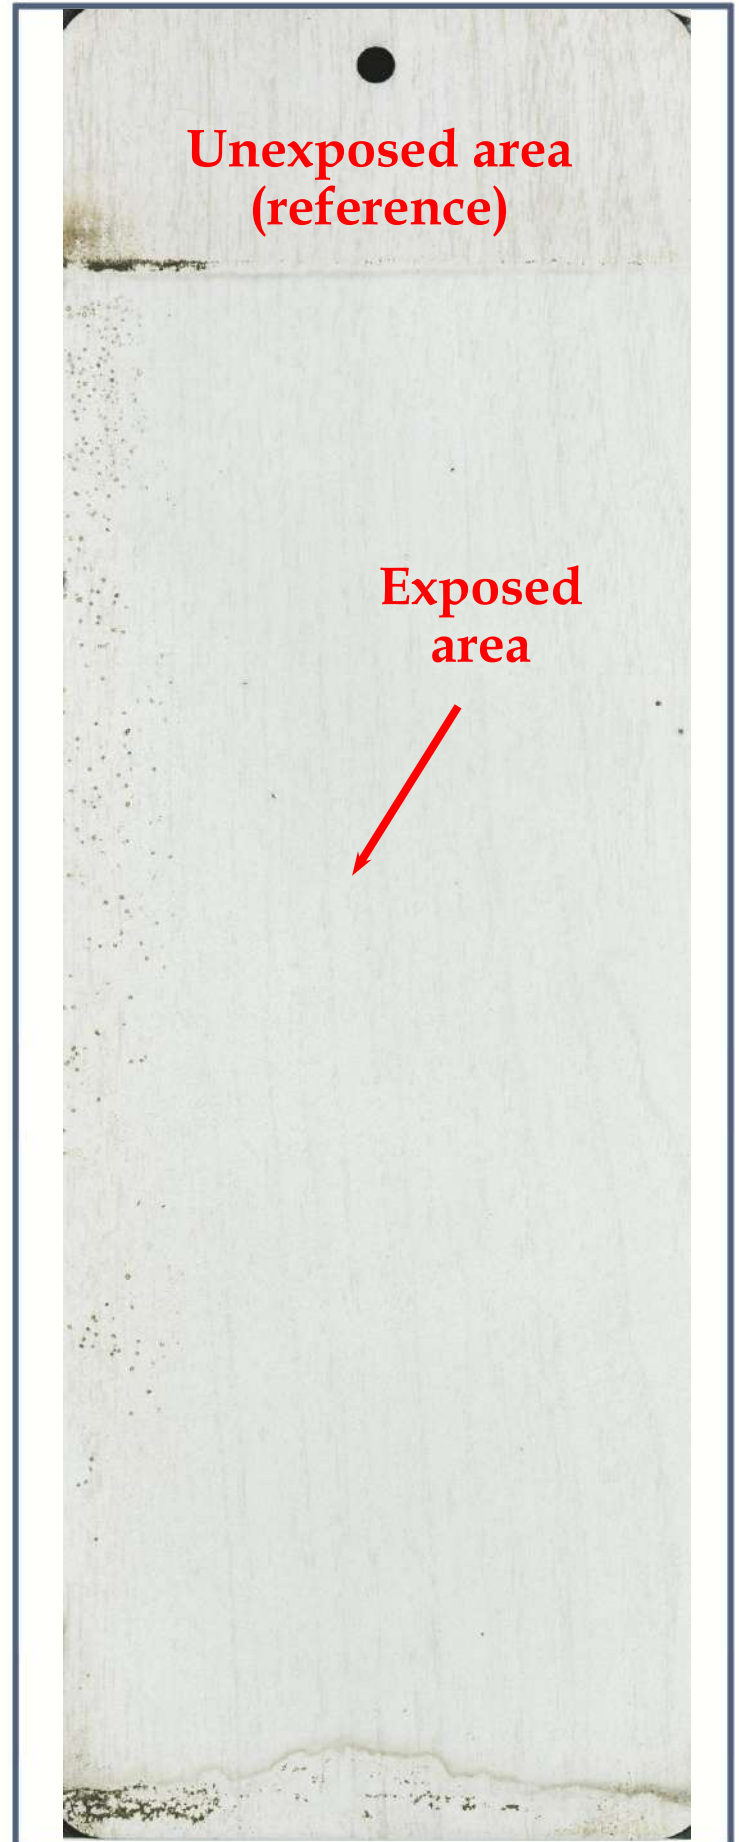



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47426  
POWDER COATING: 17G-908-A005  
HEAT TRANSFER FILM: 82501/15 L8  
colour variation ( $\Delta E$ ): 1,52  
residual gloss: 57%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47427  
POWDER COATING: 17G-908-A005  
HEAT TRANSFER FILM: 85001/02 L8  
colour variation ( $\Delta E$ ): 1,57  
residual gloss: 46%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a low residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47428  
POWDER COATING: 17C-945-A001  
HEAT TRANSFER FILM: 82531/03 L8  
colour variation ( $\Delta E$ ): **1,67**  
residual gloss: **56%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47429  
POWDER COATING: Mirror-058S25  
HEAT TRANSFER FILM: 85001/02 L8  
colour variation ( $\Delta E$ ): 1,71  
residual gloss: 57%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

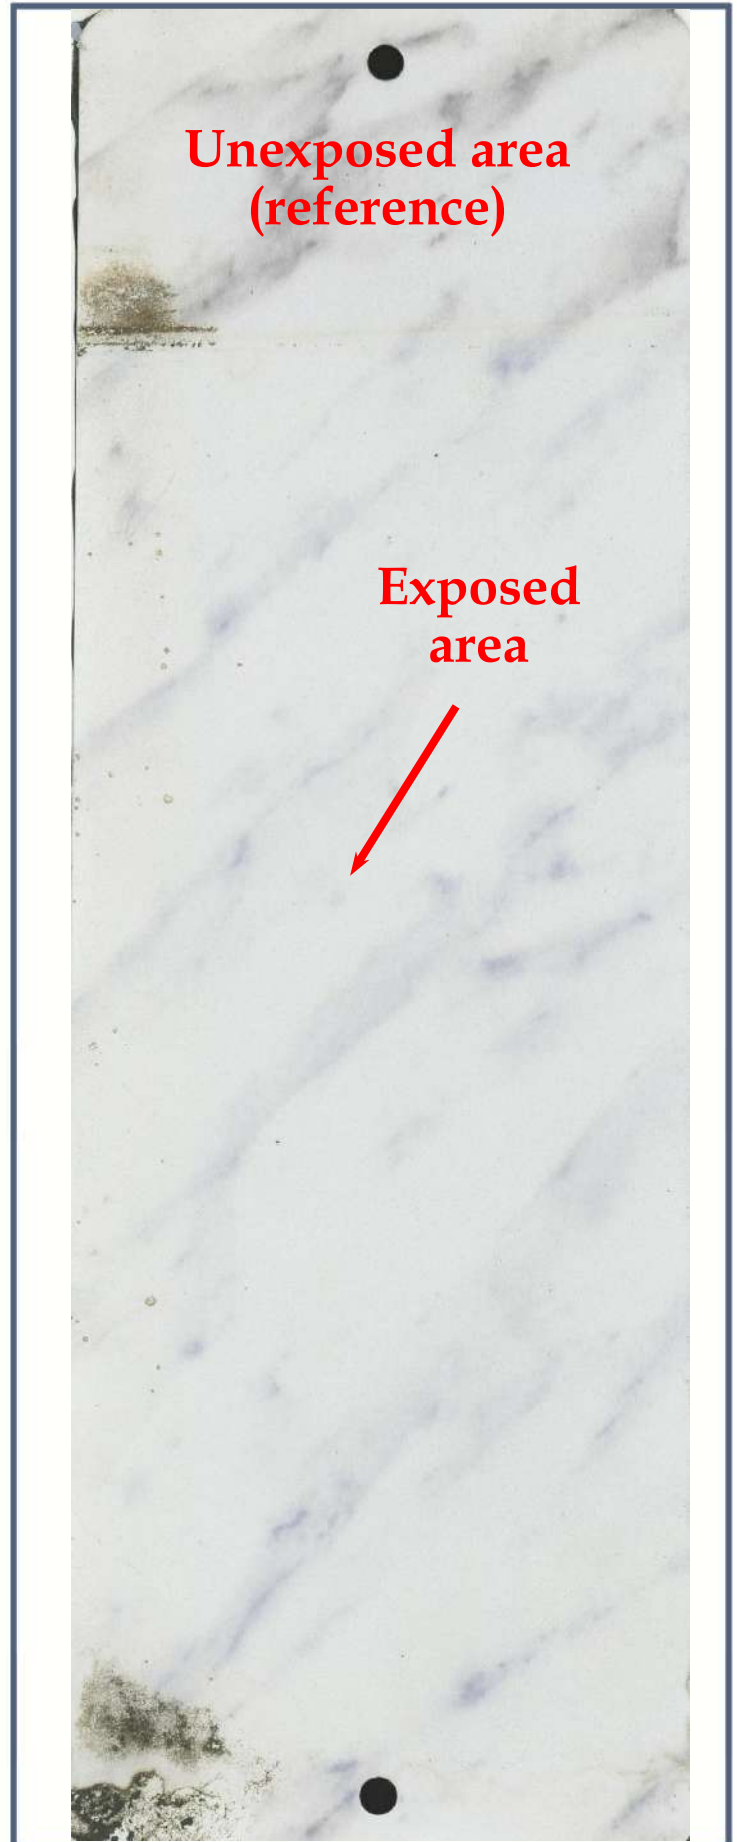



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47430  
POWDER COATING: 17G-908-A005  
HEAT TRANSFER FILM: 82531/03 L8  
colour variation ( $\Delta E$ ): 1,73  
residual gloss: 47%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a low residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

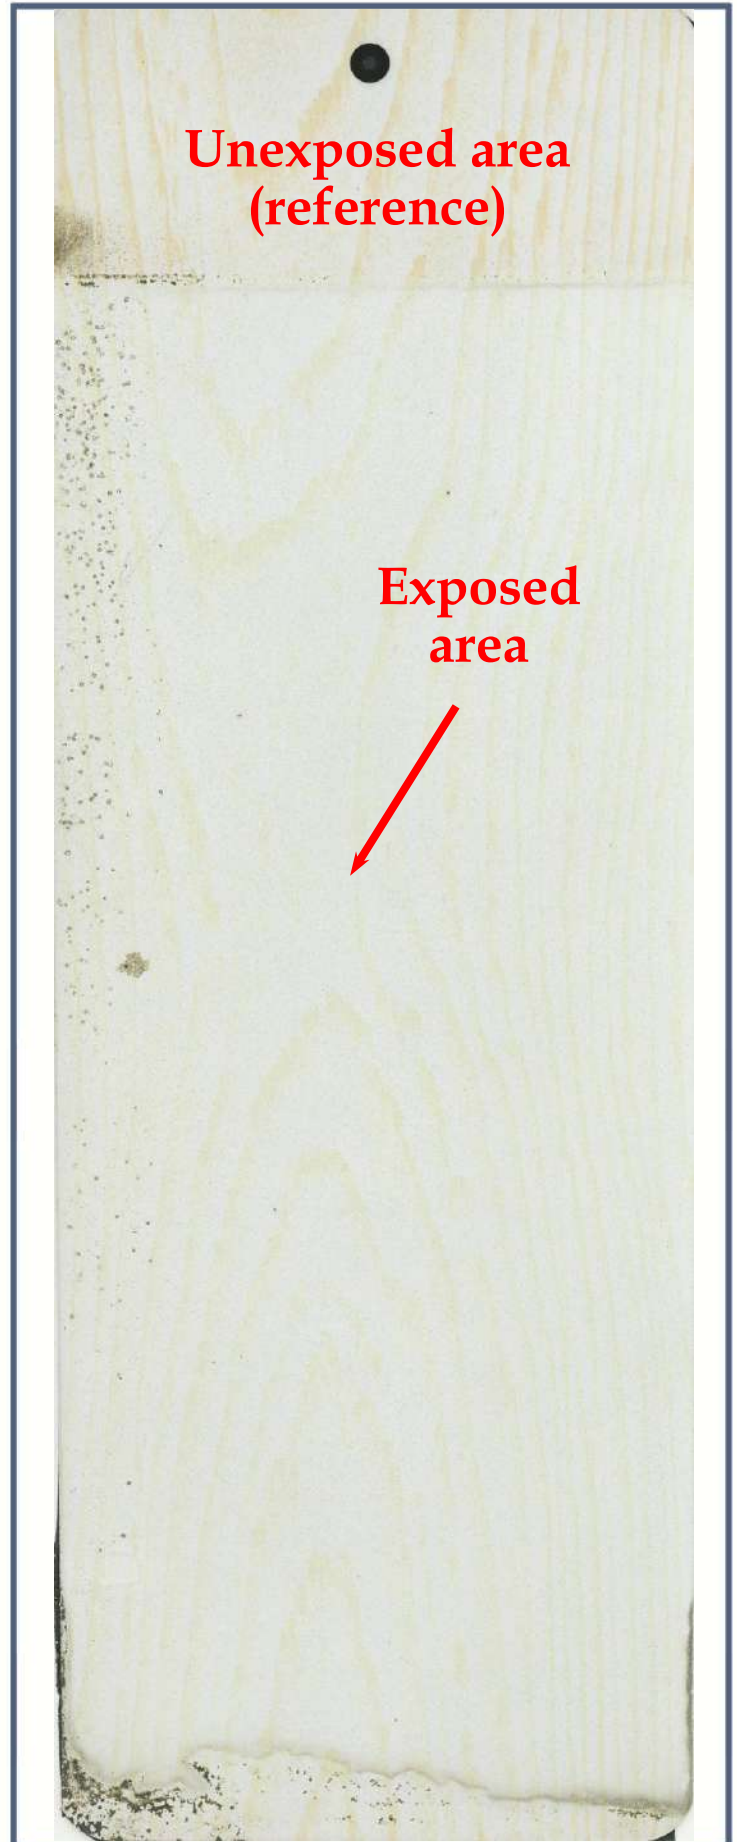





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47431  
POWDER COATING: Mirror-113S25  
HEAT TRANSFER FILM: 86053/01 L4  
colour variation ( $\Delta E$ ): 1,97  
residual gloss: 59%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

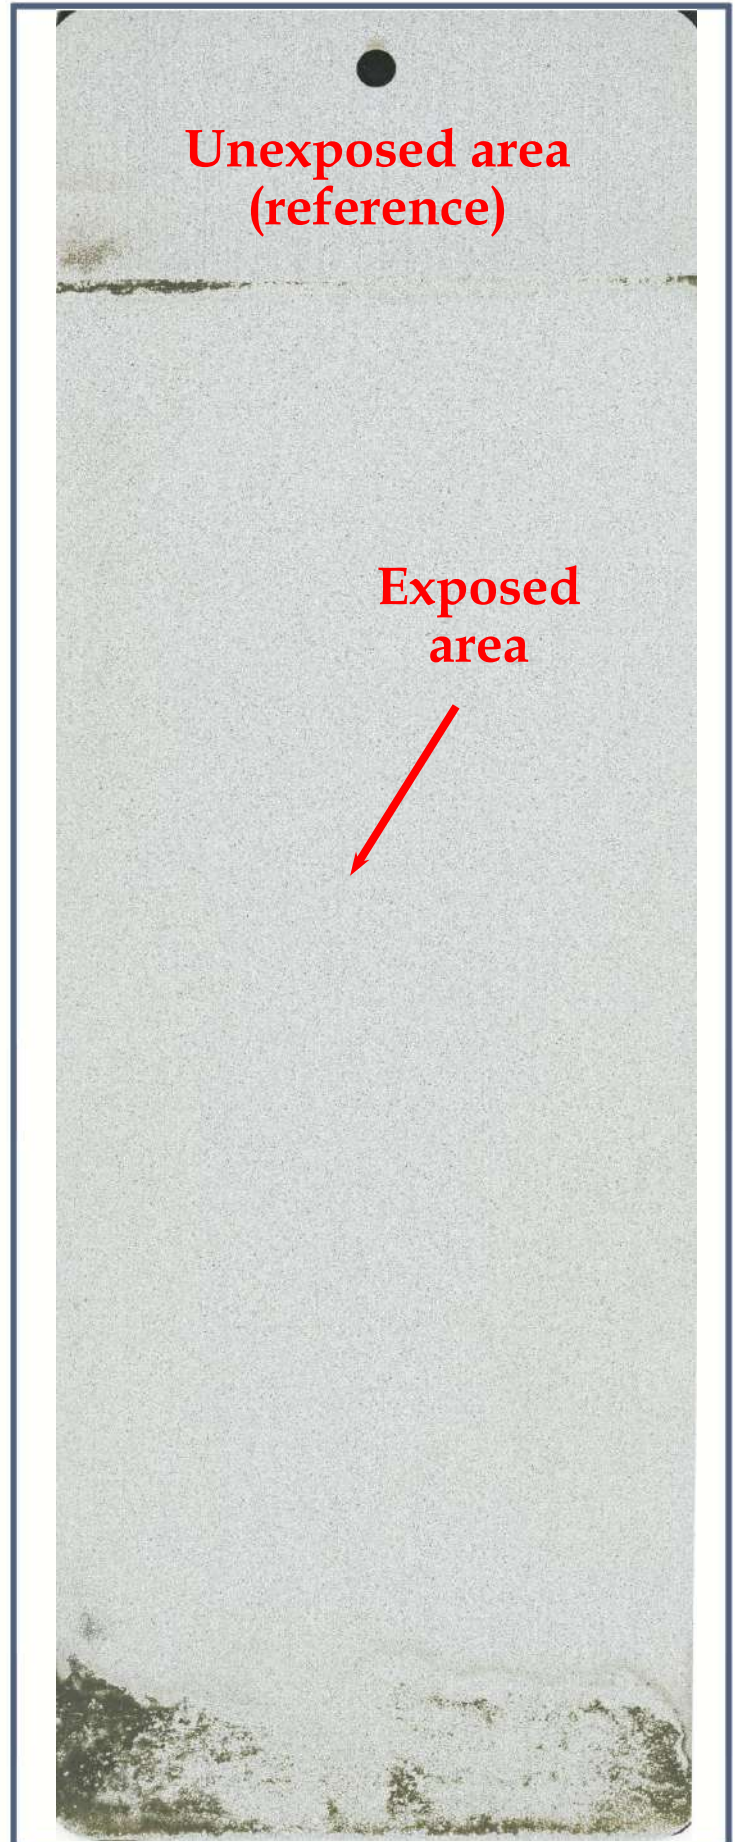



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47432  
POWDER COATING: MirrorL-183S25  
HEAT TRANSFER FILM: 86053/01 L4  
colour variation ( $\Delta E$ ): 1,98  
residual gloss: 83%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

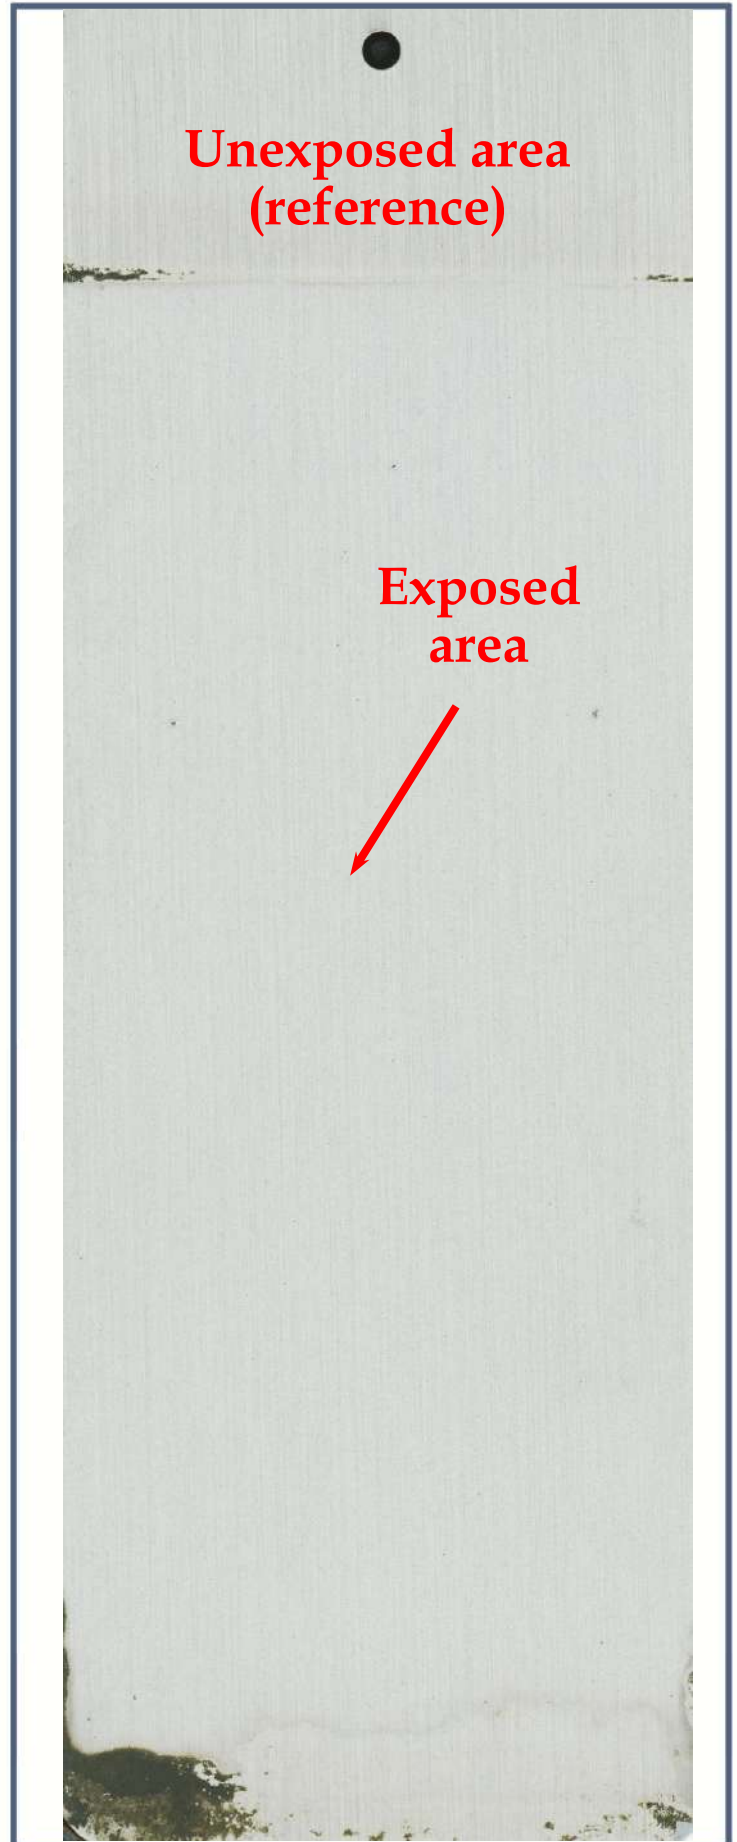





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47433  
POWDER COATING: 17C-945-A001  
HEAT TRANSFER FILM: 82305/16 L8  
colour variation ( $\Delta E$ ): 2,05  
residual gloss: 58%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47434  
POWDER COATING: 17G-945-A005  
HEAT TRANSFER FILM: 82602/04 L8  
colour variation ( $\Delta E$ ): **2,12**  
residual gloss: **63%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

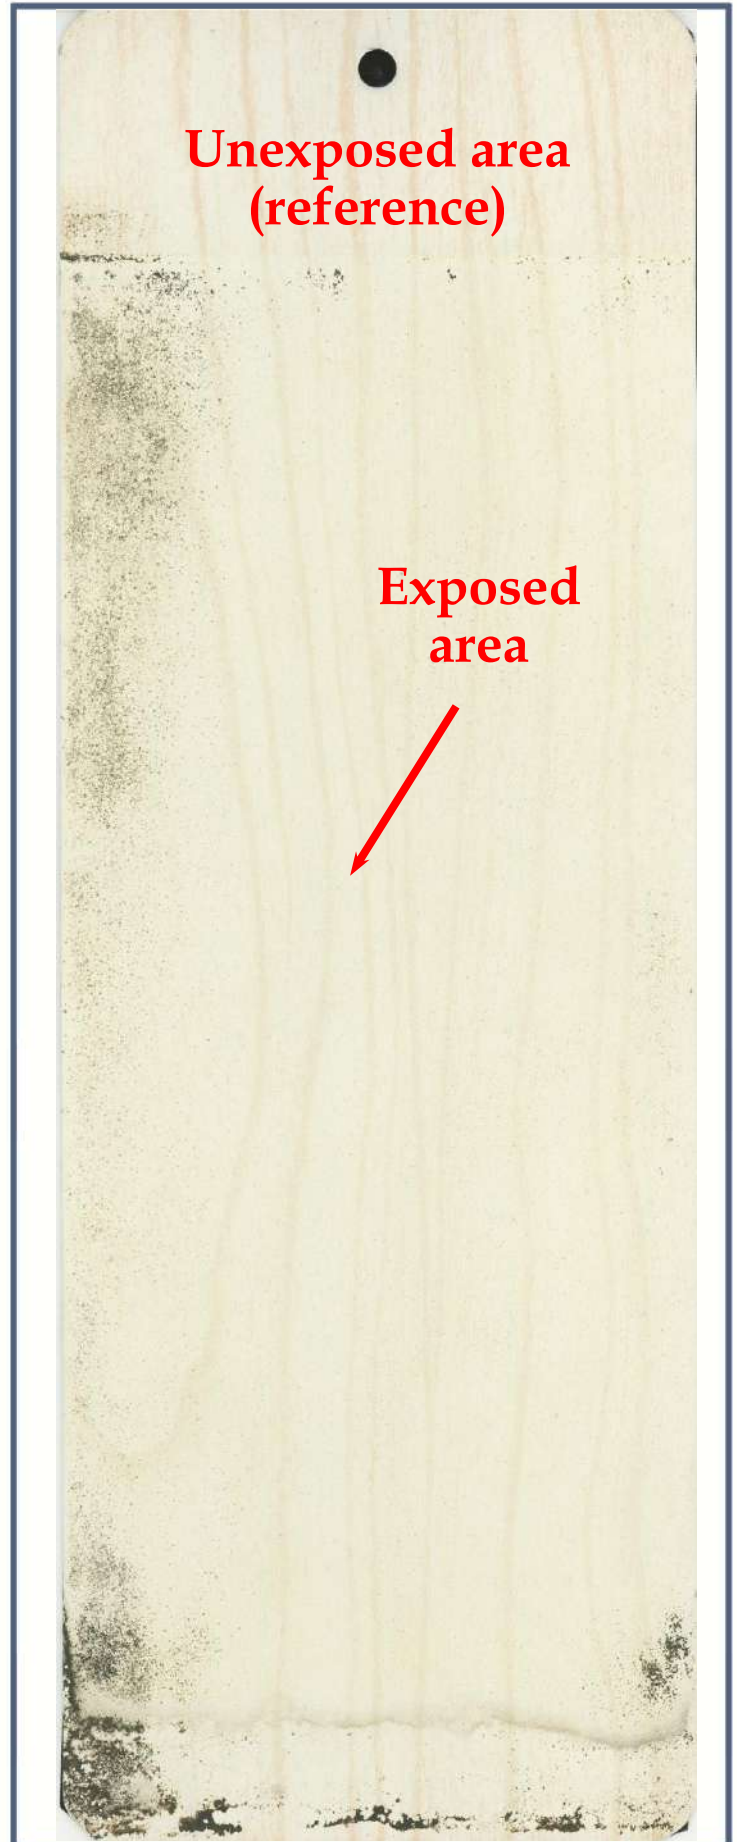



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47435  
POWDER COATING: 17G-945-A005  
HEAT TRANSFER FILM: 82513/04 L8  
colour variation ( $\Delta E$ ): 2,26  
residual gloss: 55%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and normal colour variation, the aspect still remains good.




Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**

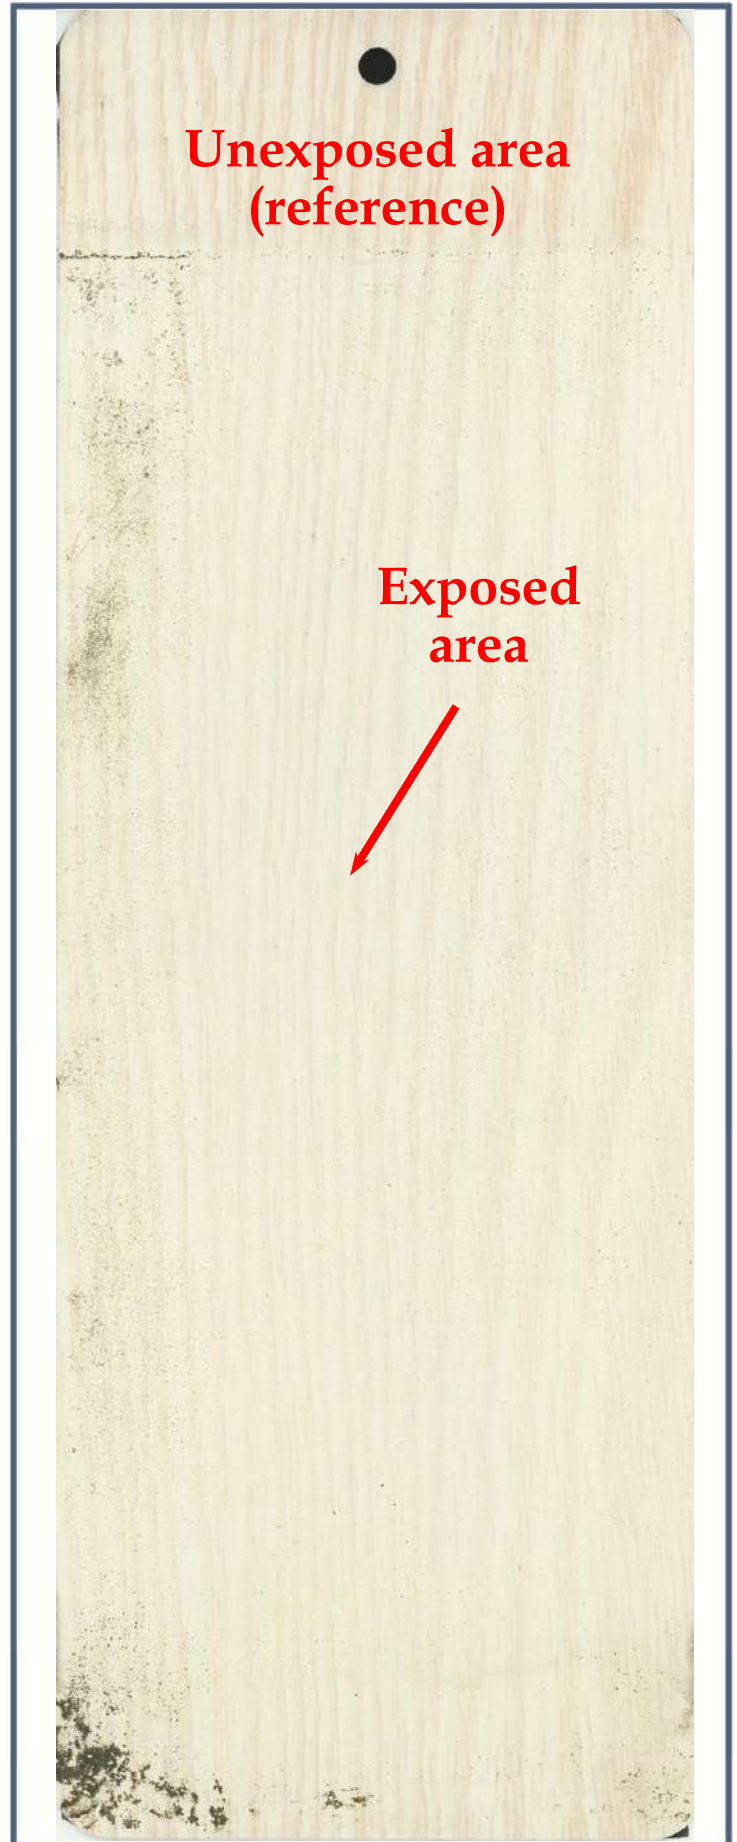





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47436  
POWDER COATING: Mirror-058S25  
HEAT TRANSFER FILM: 85014/03 L4  
colour variation ( $\Delta E$ ): 2,31  
residual gloss: 60%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

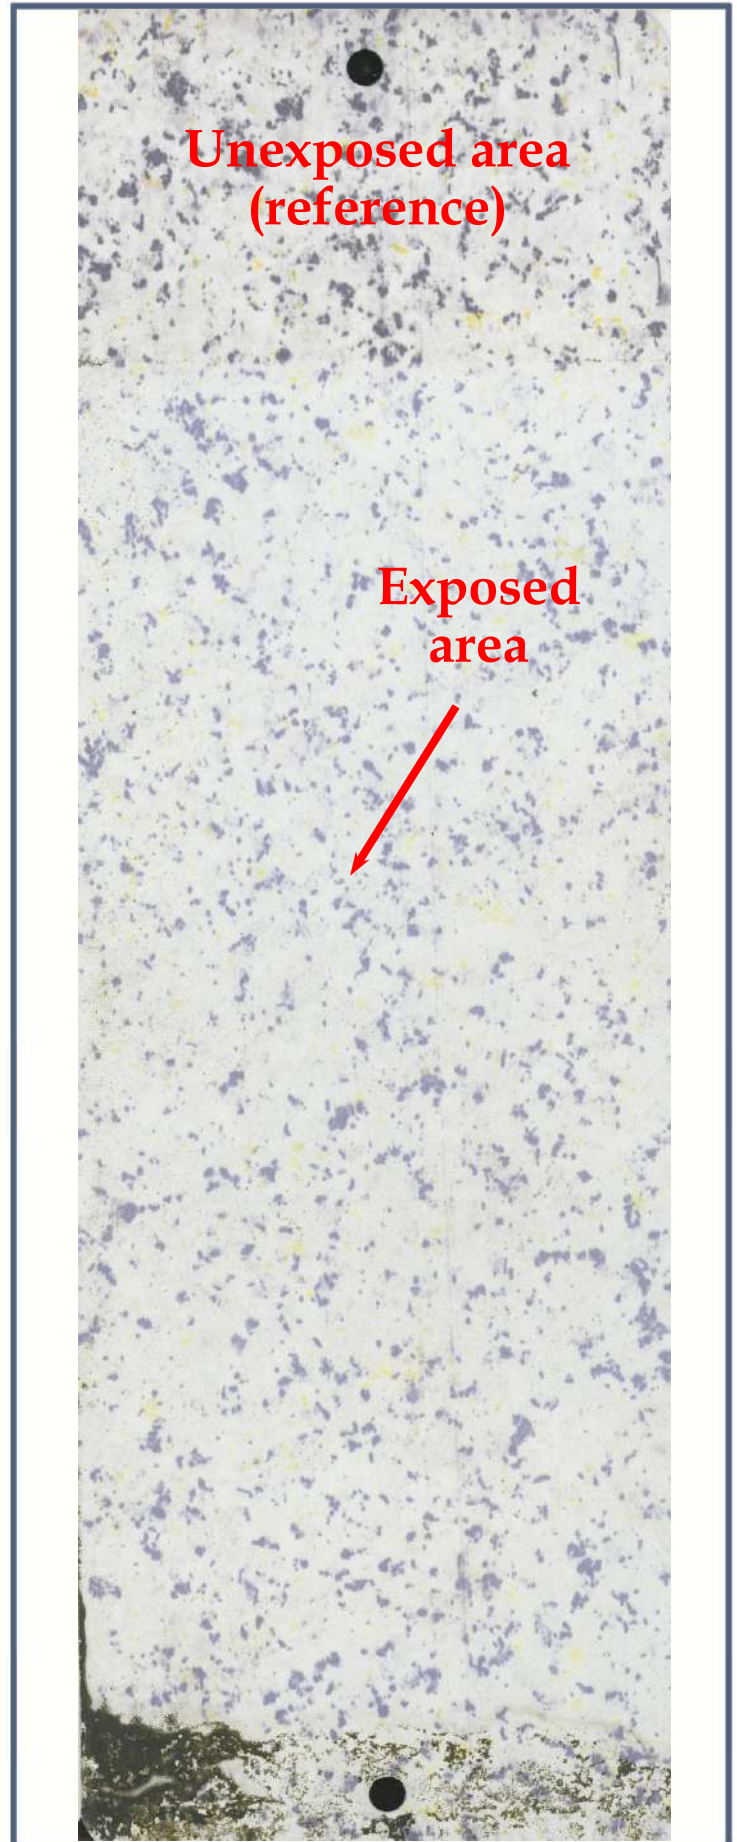

**Unexposed area  
(reference)**

**Exposed  
area**





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47437  
POWDER COATING: Mirror-113S25  
HEAT TRANSFER FILM: 86047/15 L4  
colour variation ( $\Delta E$ ): **2,34**  
residual gloss: **68%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

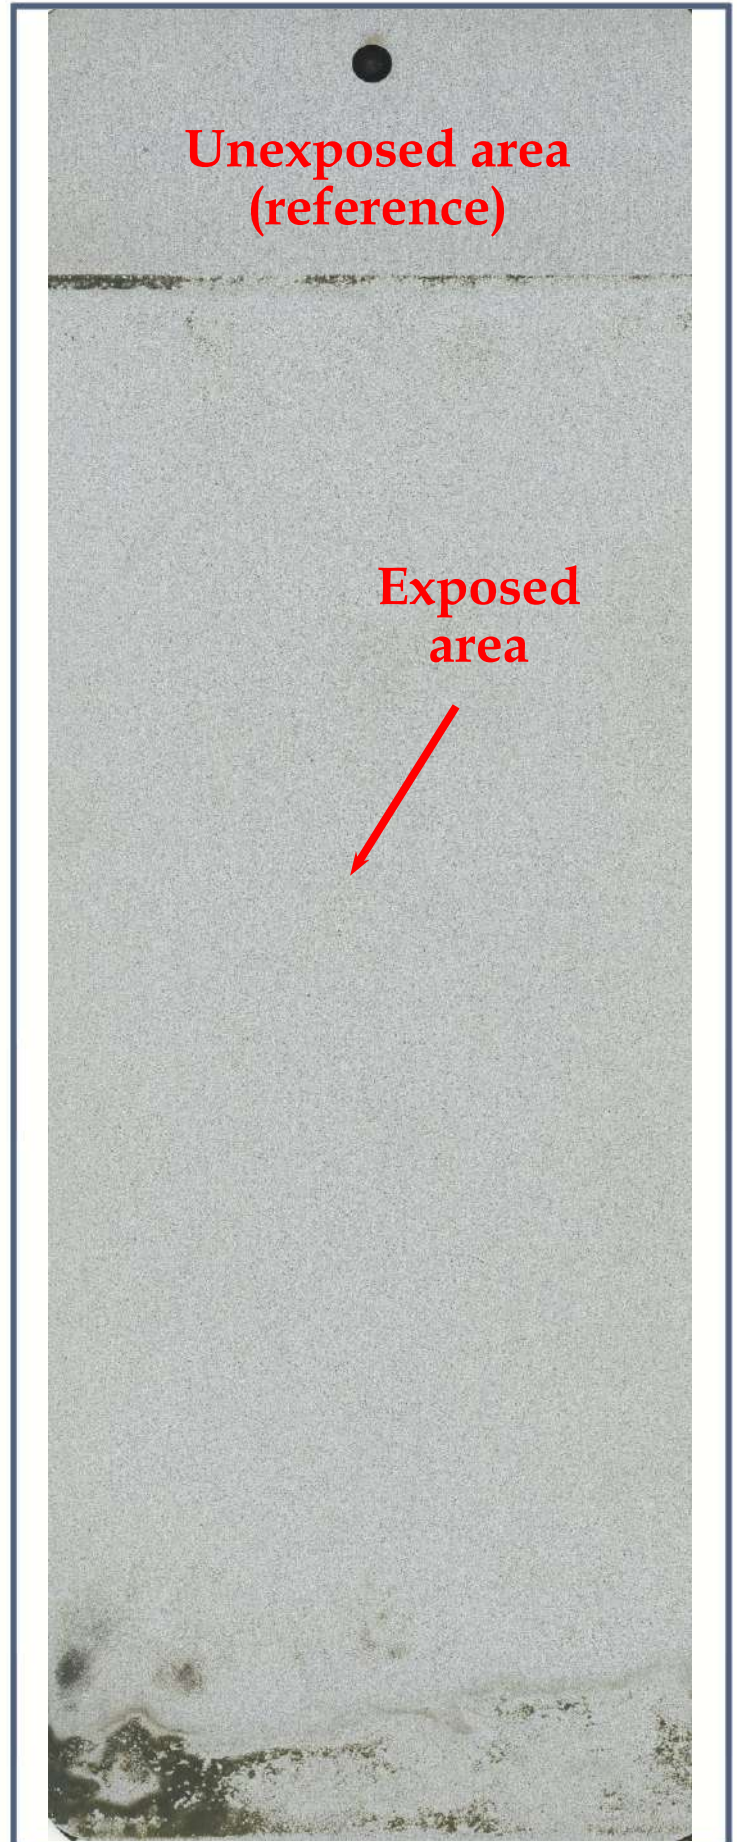



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47438  
POWDER COATING: 17C-945-A001  
HEAT TRANSFER FILM: 82602/04 L8  
colour variation ( $\Delta E$ ): 2,50  
residual gloss: 68%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47439  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 81502/02 L4  
colour variation ( $\Delta E$ ): **2,61**  
residual gloss: 55%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47440  
POWDER COATING: 17G-945-A005  
HEAT TRANSFER FILM: 82305/16 L8  
colour variation ( $\Delta E$ ): **2,64**  
residual gloss: 53%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.




Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**

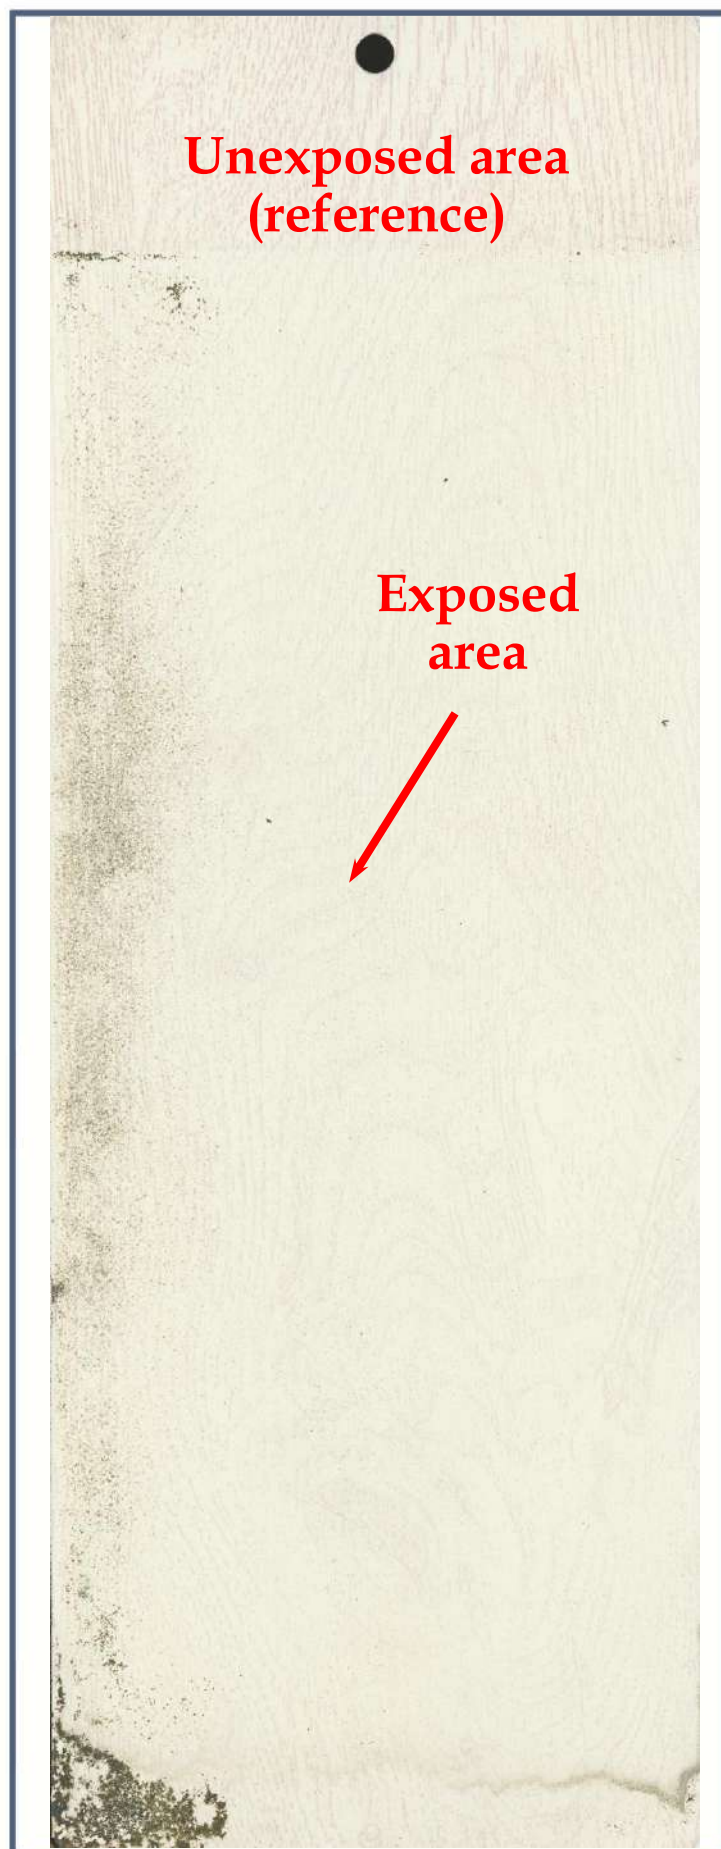



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47441  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82602/04 L8  
colour variation ( $\Delta E$ ): **2,81**  
residual gloss: **65%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47442  
POWDER COATING: 17C-908-A001  
HEAT TRANSFER FILM: 82531/03 L8  
colour variation ( $\Delta E$ ): 2,82  
residual gloss: 44%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47443  
POWDER COATING: 17C-945-A001  
HEAT TRANSFER FILM: 82513/04 L8  
colour variation ( $\Delta E$ ): 2,96  
residual gloss: 55%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47444  
POWDER COATING: 17C-906-A001  
HEAT TRANSFER FILM: 81401/01 L4  
colour variation ( $\Delta E$ ): 2,96  
residual gloss: 57%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47445  
POWDER COATING: MirrorL-183S25  
HEAT TRANSFER FILM: 86047/15 L4  
colour variation ( $\Delta E$ ): **3,04**  
residual gloss: **87%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

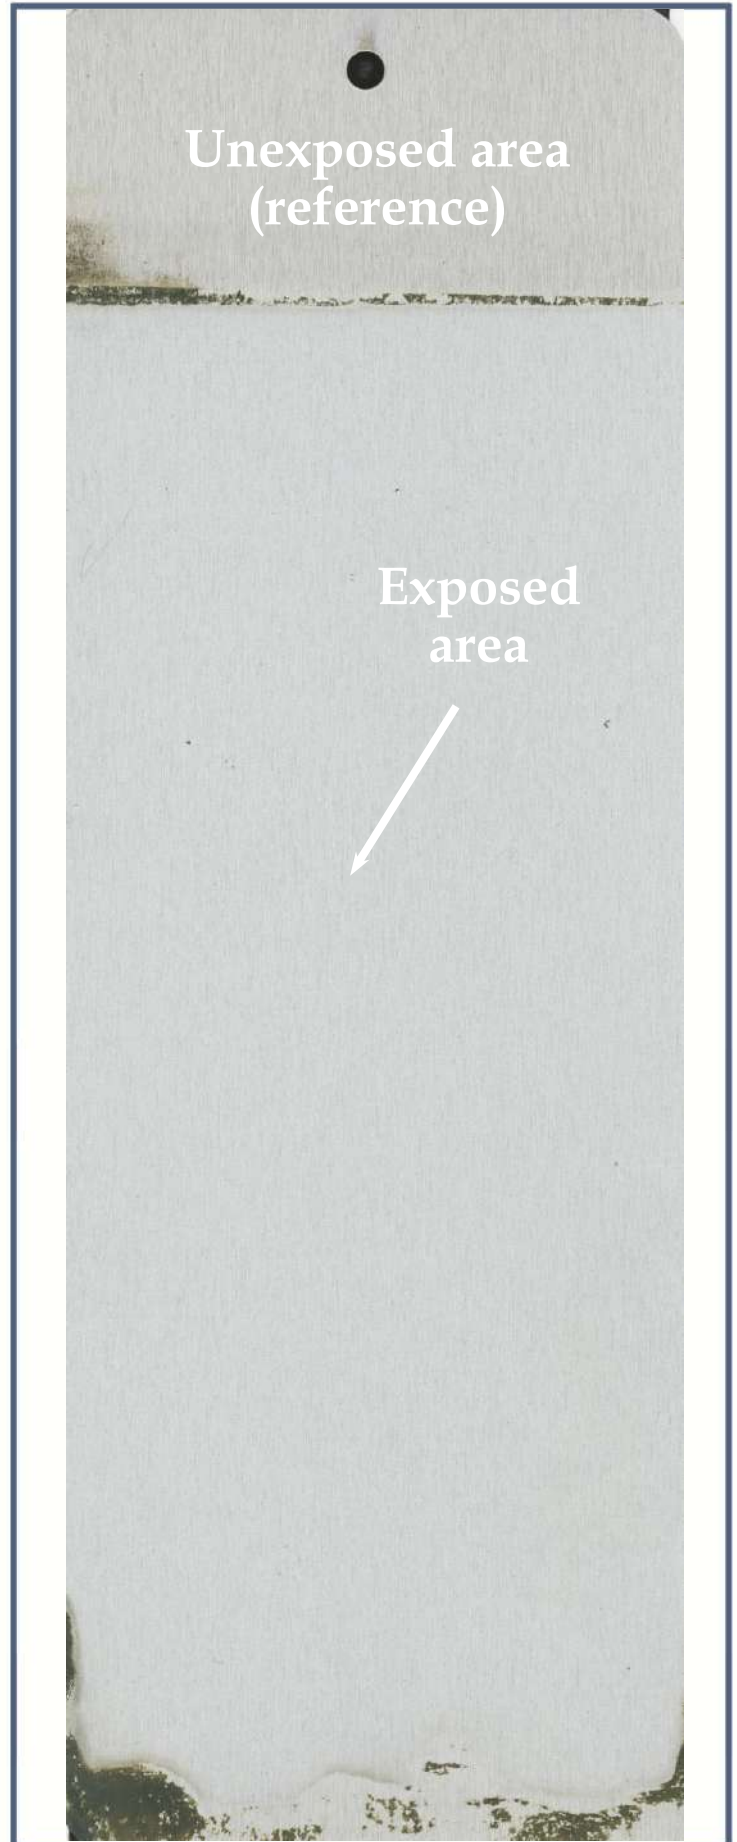





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47446  
POWDER COATING: Mirror-113S25  
HEAT TRANSFER FILM: 86047/04 L4  
colour variation ( $\Delta E$ ): 3,15  
residual gloss: 54%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

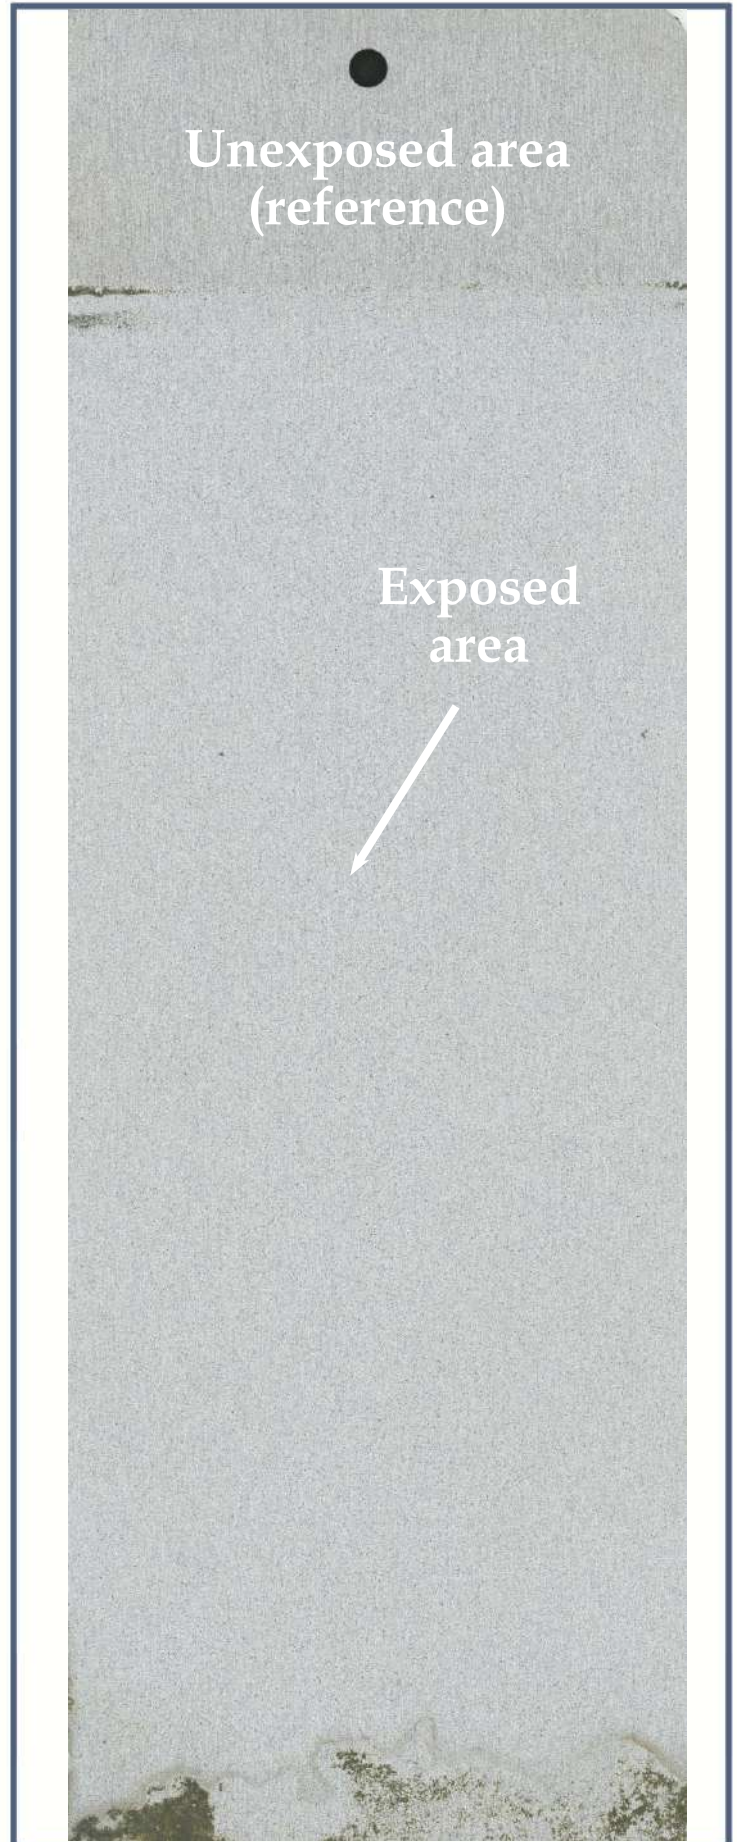



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47447  
POWDER COATING: 17C-908-A001  
HEAT TRANSFER FILM: 81304/02 L8  
colour variation ( $\Delta E$ ): 3,21  
residual gloss: 52%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47448  
POWDER COATING: 17C-908-A001  
HEAT TRANSFER FILM: 82505/10 L8  
colour variation ( $\Delta E$ ): **3,33**  
residual gloss: **57%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47449  
POWDER COATING: Mirror-058S25  
HEAT TRANSFER FILM: 85014/01 L4  
colour variation ( $\Delta E$ ): 3,36  
residual gloss: 46%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

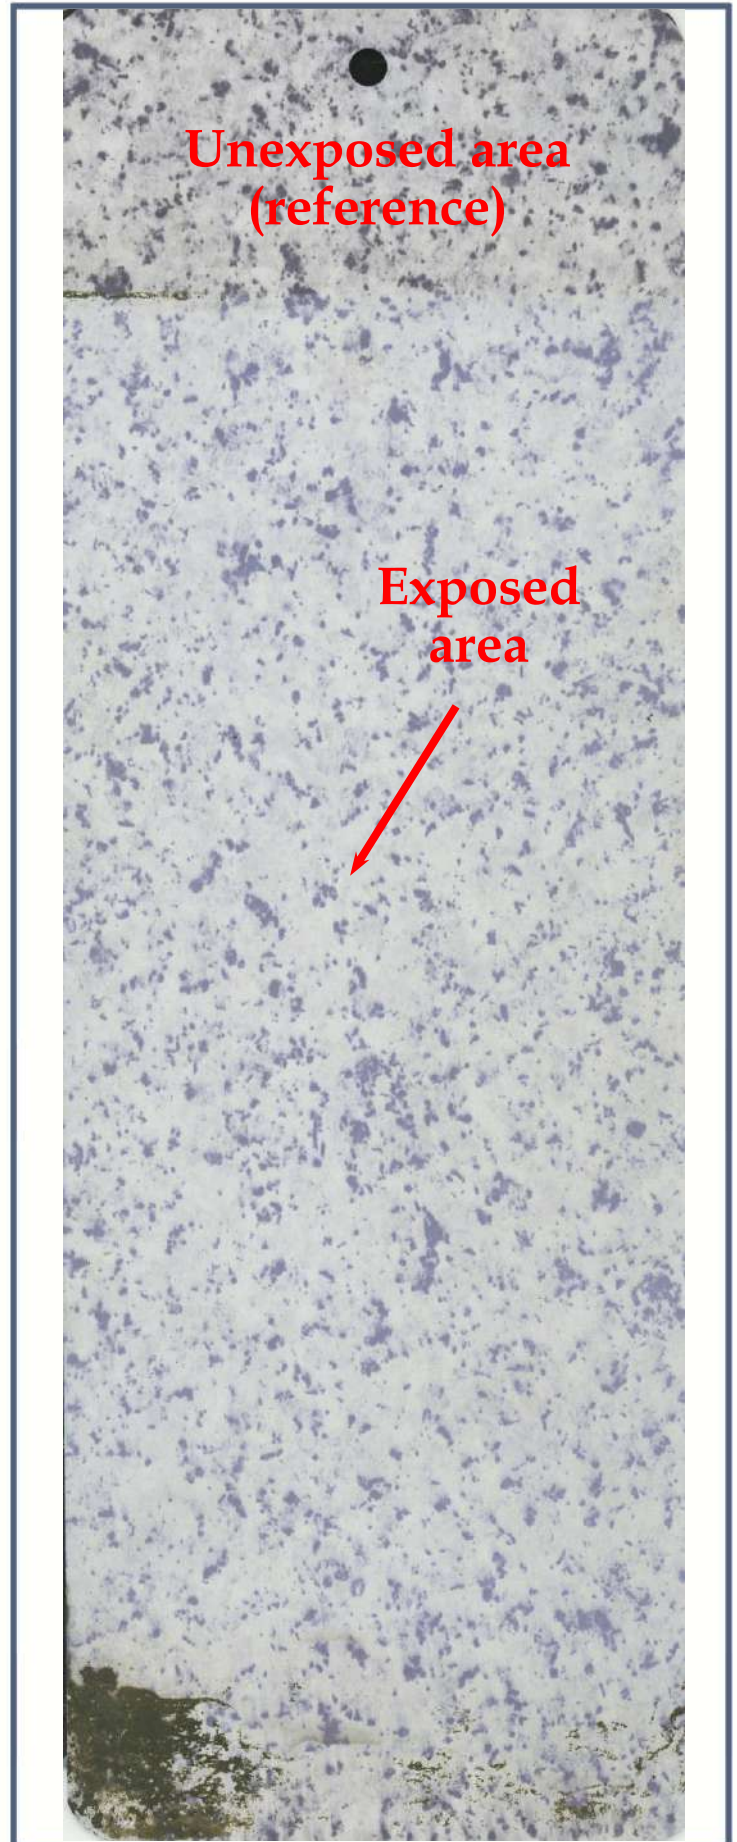



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47450  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82501/05 L4  
colour variation ( $\Delta E$ ): 3,38  
residual gloss: 67%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47451  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82118/01 L4  
colour variation ( $\Delta E$ ): **3,40**  
residual gloss: **68%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47452  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82503/12 L4  
colour variation ( $\Delta E$ ): **3,46**  
residual gloss: **59%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

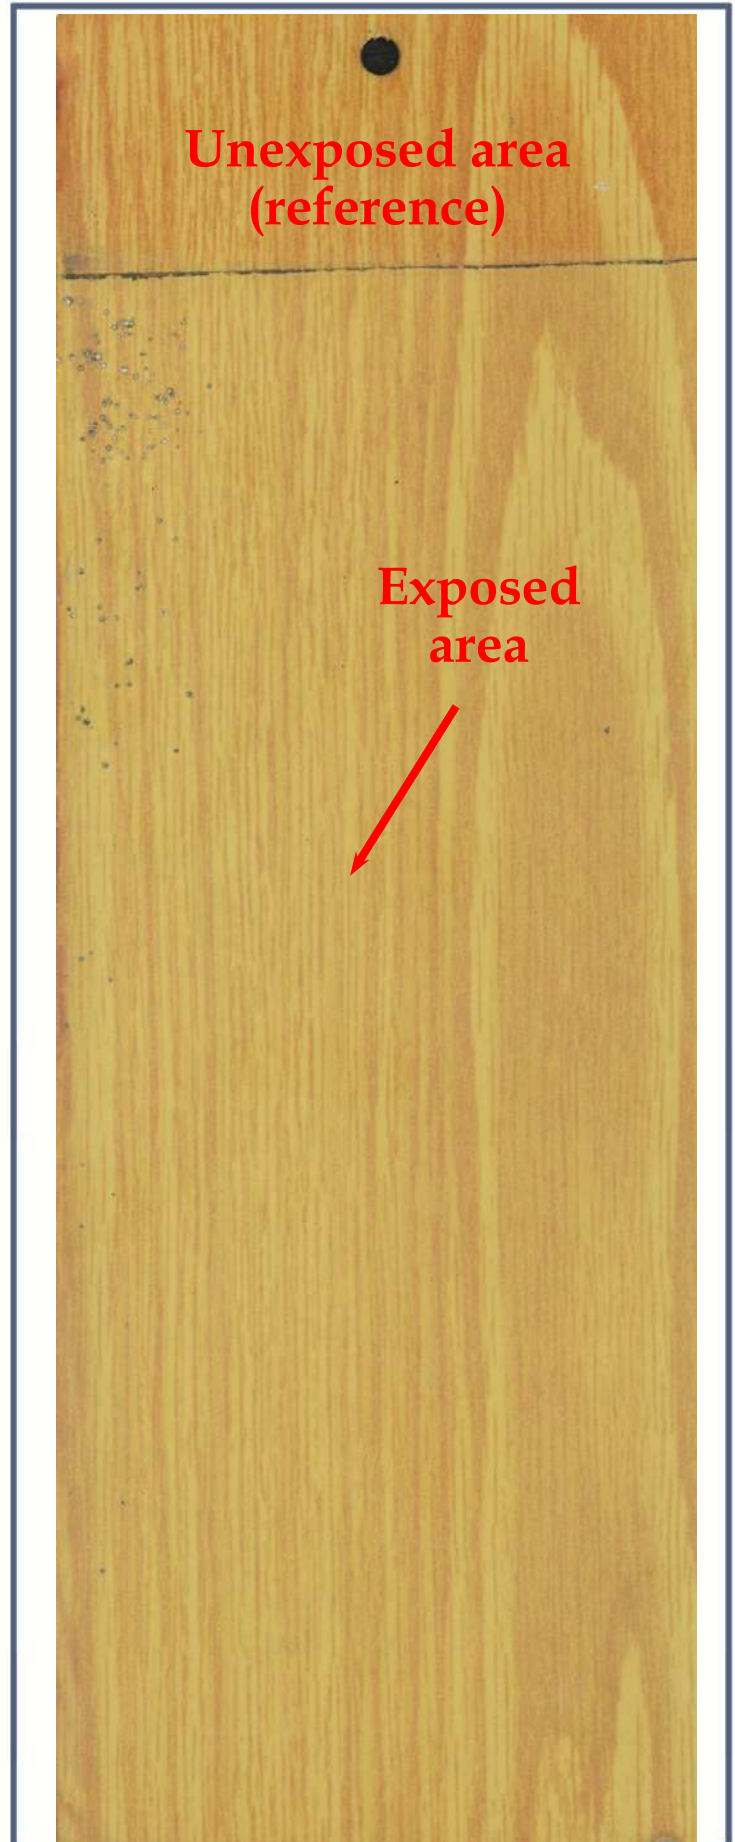



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47453  
POWDER COATING: 17C-908-A001  
HEAT TRANSFER FILM: 82501/15 L8  
colour variation ( $\Delta E$ ): **3,51**  
residual gloss: **51%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47454  
POWDER COATING: 17C-942-A001  
HEAT TRANSFER FILM: 82531/01 L4  
colour variation ( $\Delta E$ ): 3,59  
residual gloss: 52%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47455  
POWDER COATING: MirrorL-183S25  
HEAT TRANSFER FILM: 86047/04 L4  
colour variation ( $\Delta E$ ): 3,71  
residual gloss: 87%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

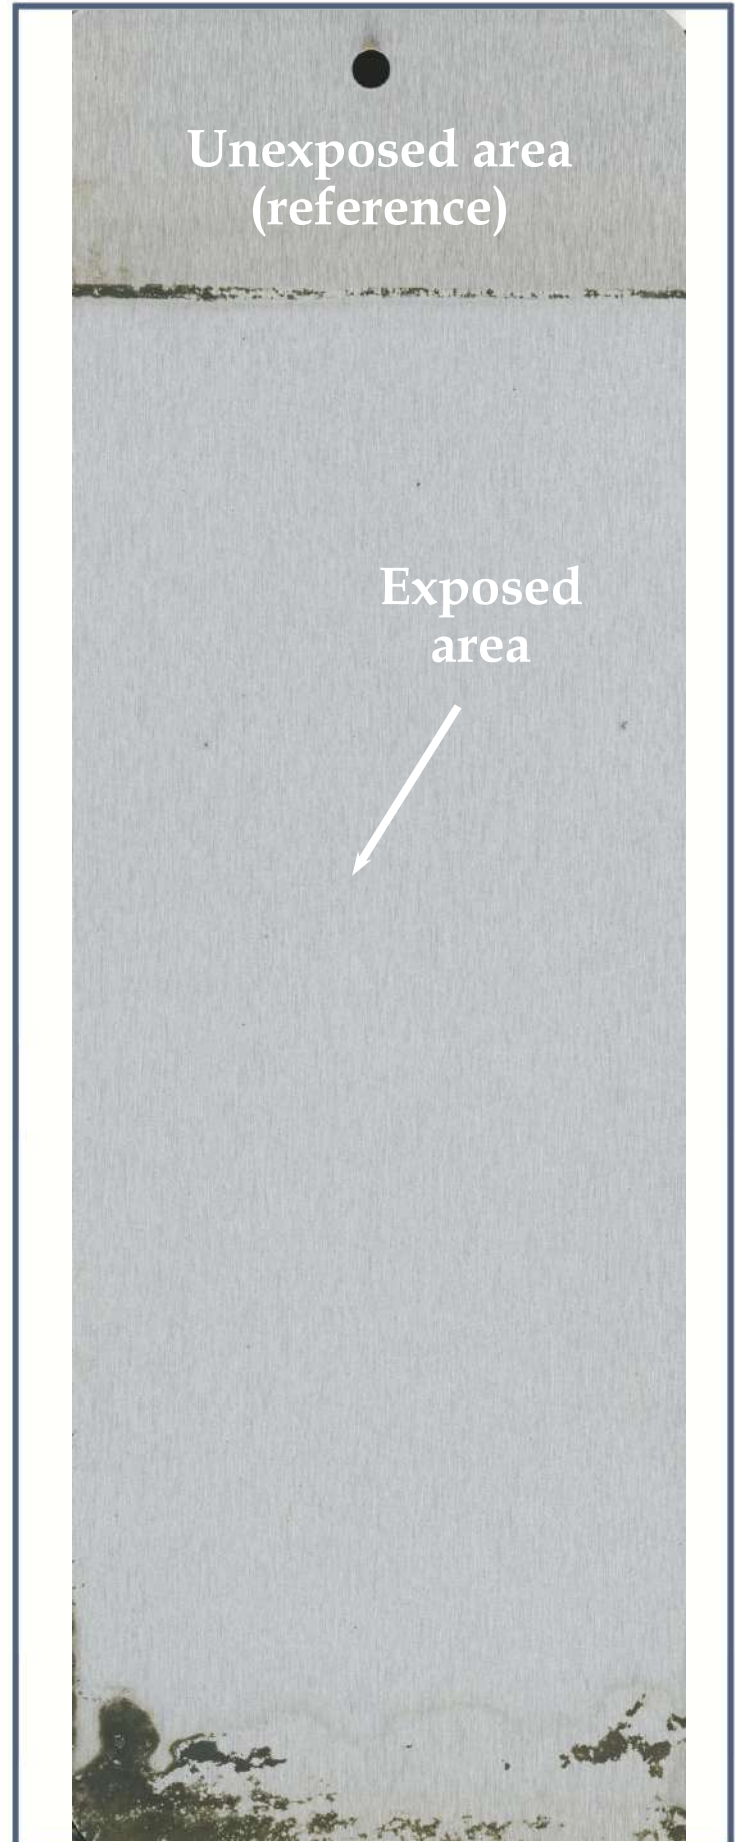



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47456  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 81304/01 L4  
colour variation ( $\Delta E$ ): 3,77  
residual gloss: 82%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

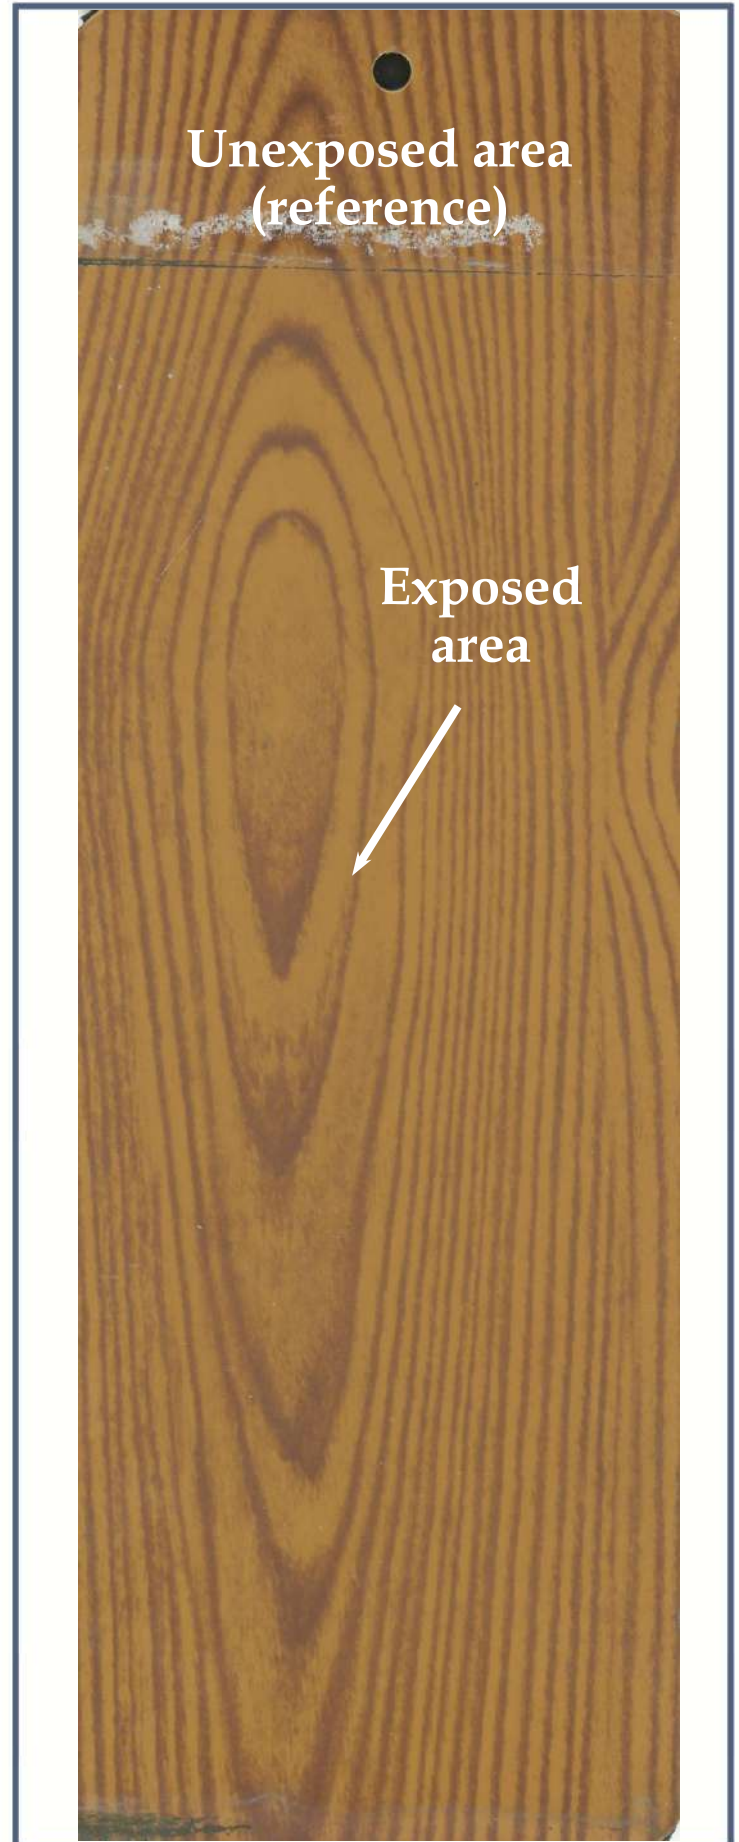





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47457  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 82308/21 L4  
colour variation ( $\Delta E$ ): **3,84**  
residual gloss: **65%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).



**Unexposed area  
(reference)**

**Exposed  
area**





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47458  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 81412/03 L4  
colour variation ( $\Delta E$ ): **3,91**  
residual gloss: **78%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

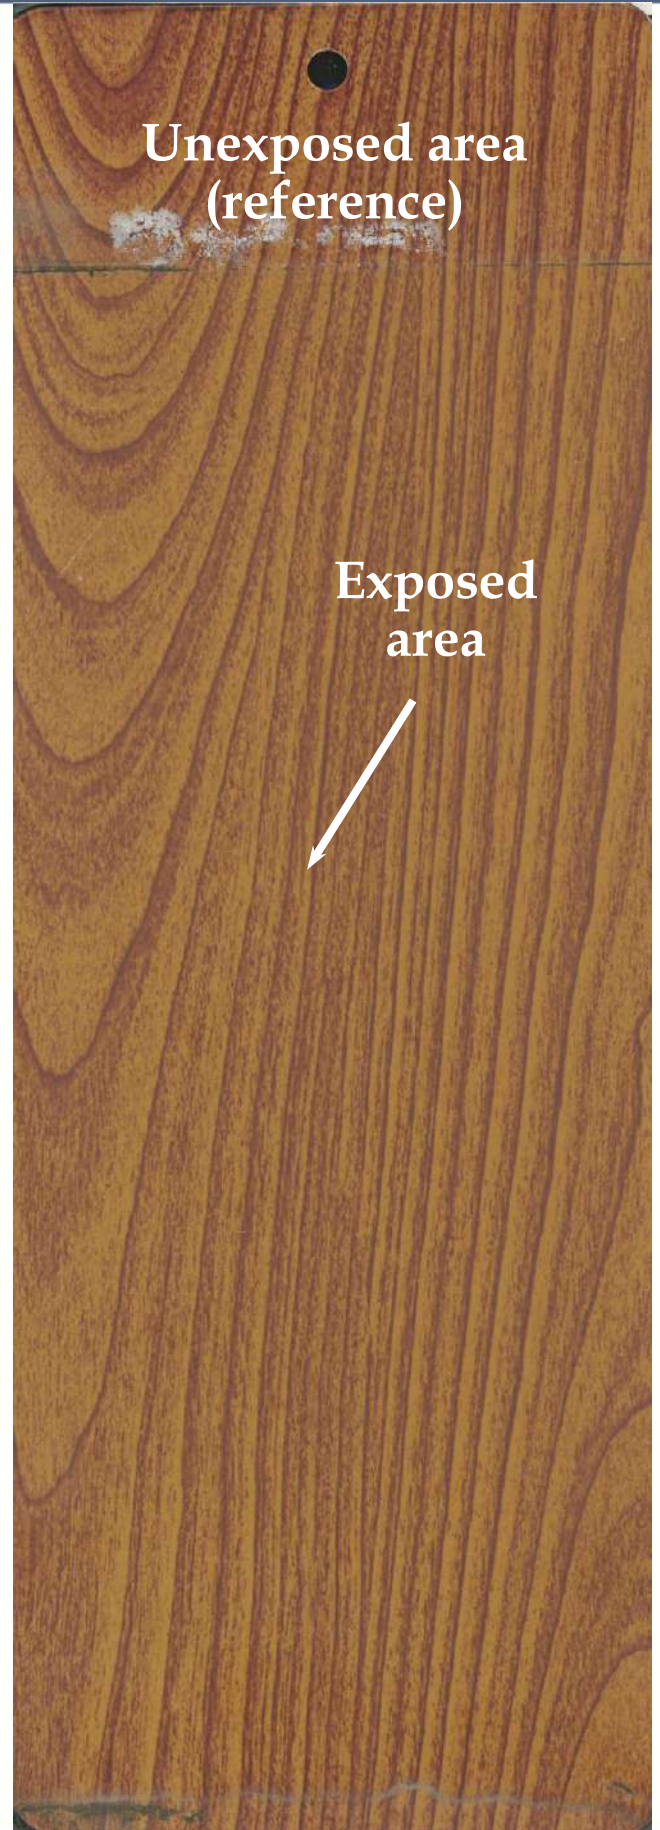





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47459  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 82531/02 L4  
colour variation ( $\Delta E$ ): **3,92**  
residual gloss: **81%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

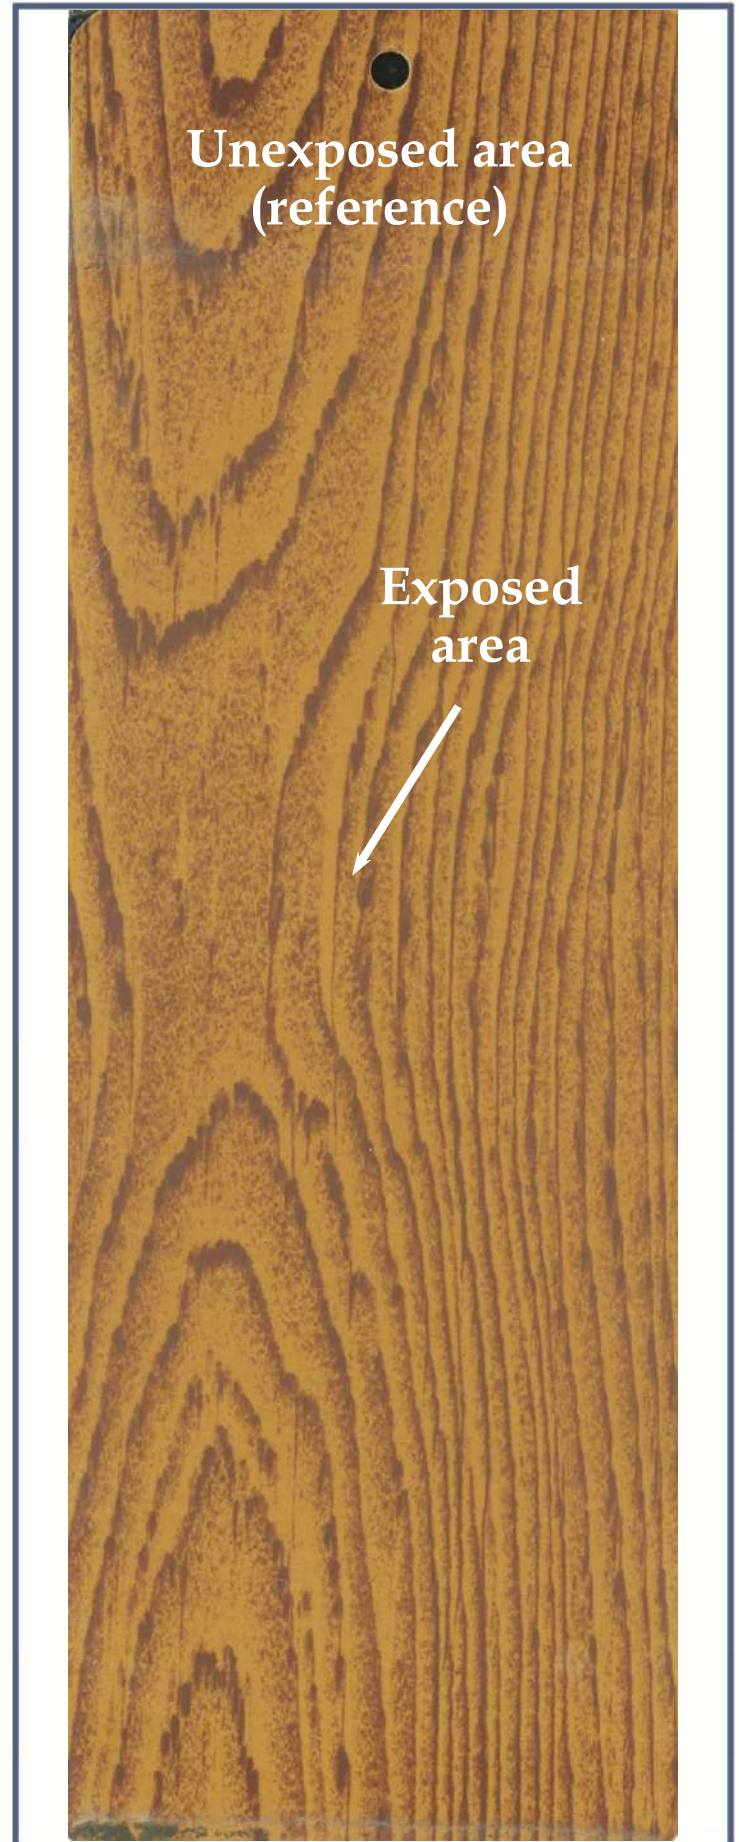



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47460  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82506/02 L4  
colour variation ( $\Delta E$ ): 3,97  
residual gloss: 77%


### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

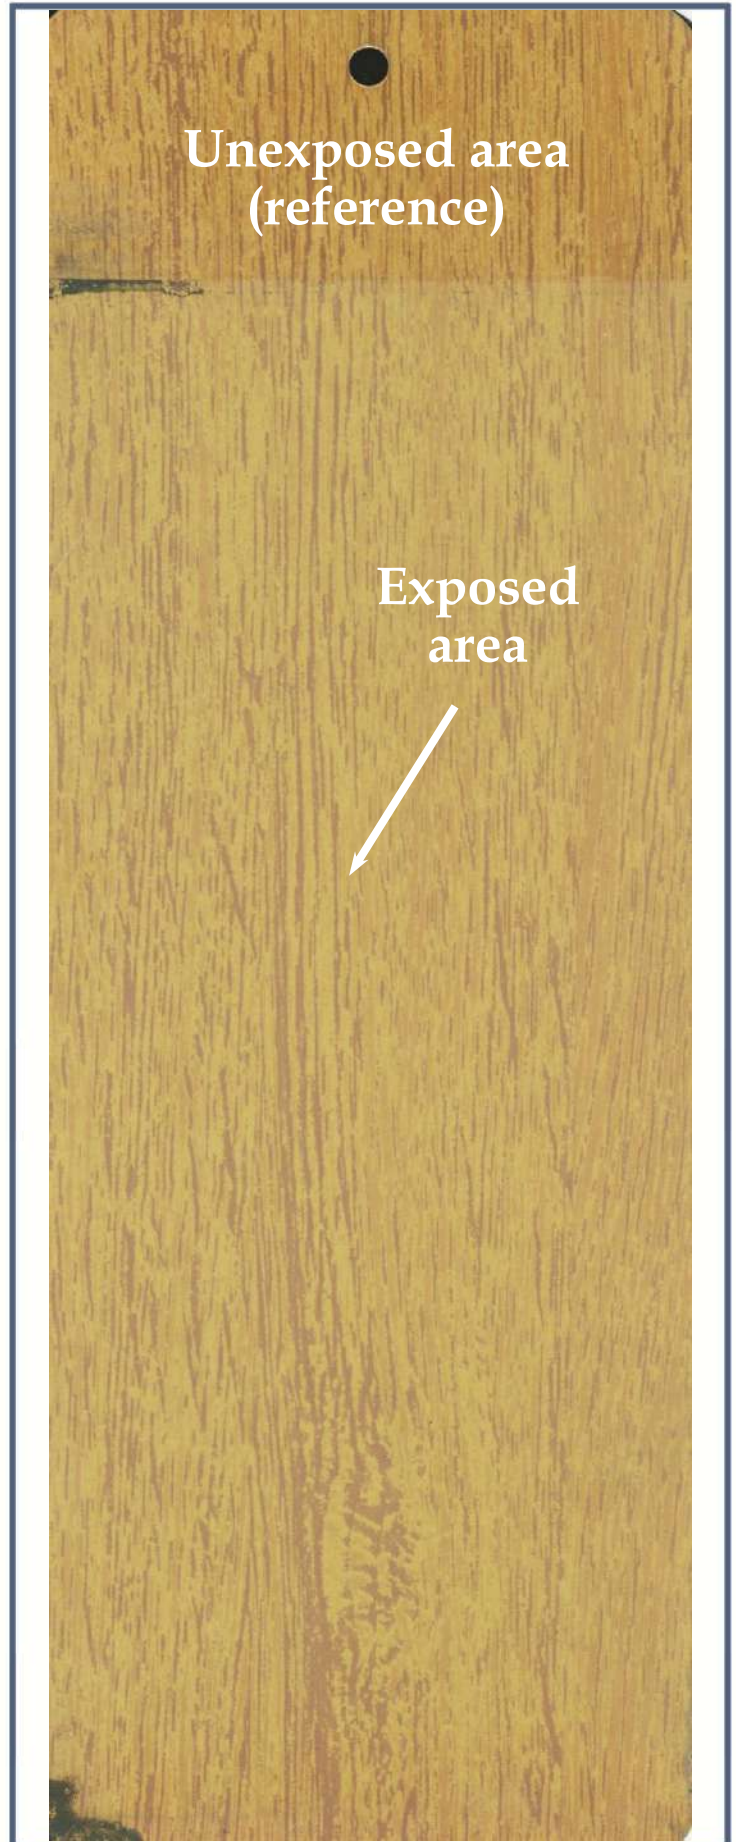





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47461  
POWDER COATING: 17C-942-A001  
HEAT TRANSFER FILM: 82602/02 L4  
colour variation ( $\Delta E$ ): **4,01**  
residual gloss: **48%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

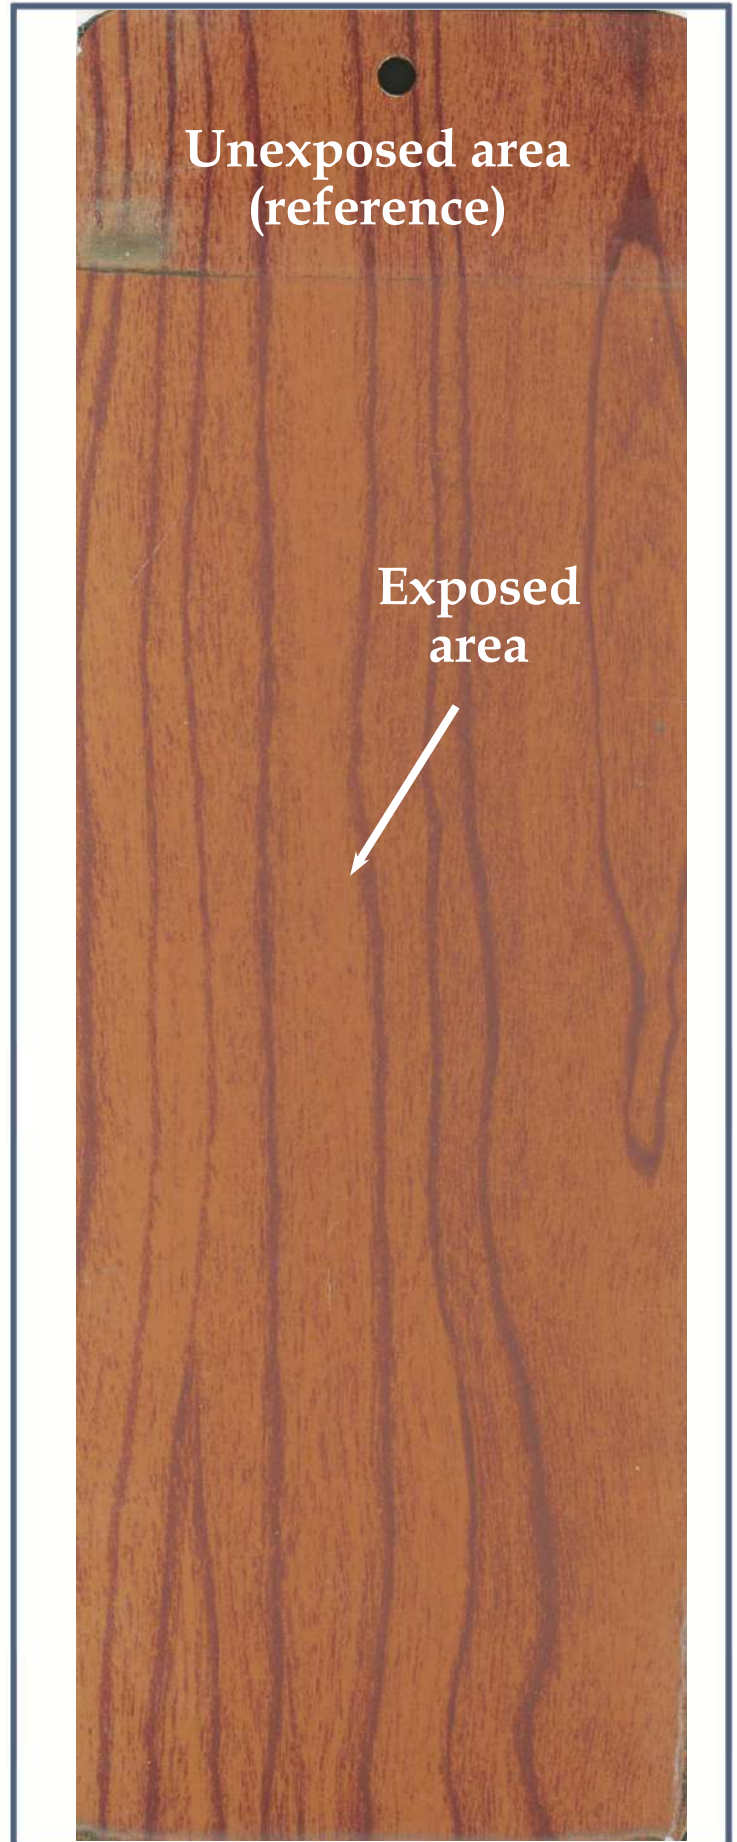



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47462  
POWDER COATING: 17C-942-A001  
HEAT TRANSFER FILM: 81412/03 L4  
colour variation ( $\Delta E$ ): **4,04**  
residual gloss: **52%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47462  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 82505/02 L4  
colour variation ( $\Delta E$ ): **4,14**  
residual gloss: 72%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47464  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82502/01 L4  
colour variation ( $\Delta E$ ): **4,15**  
residual gloss: **62%**


### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

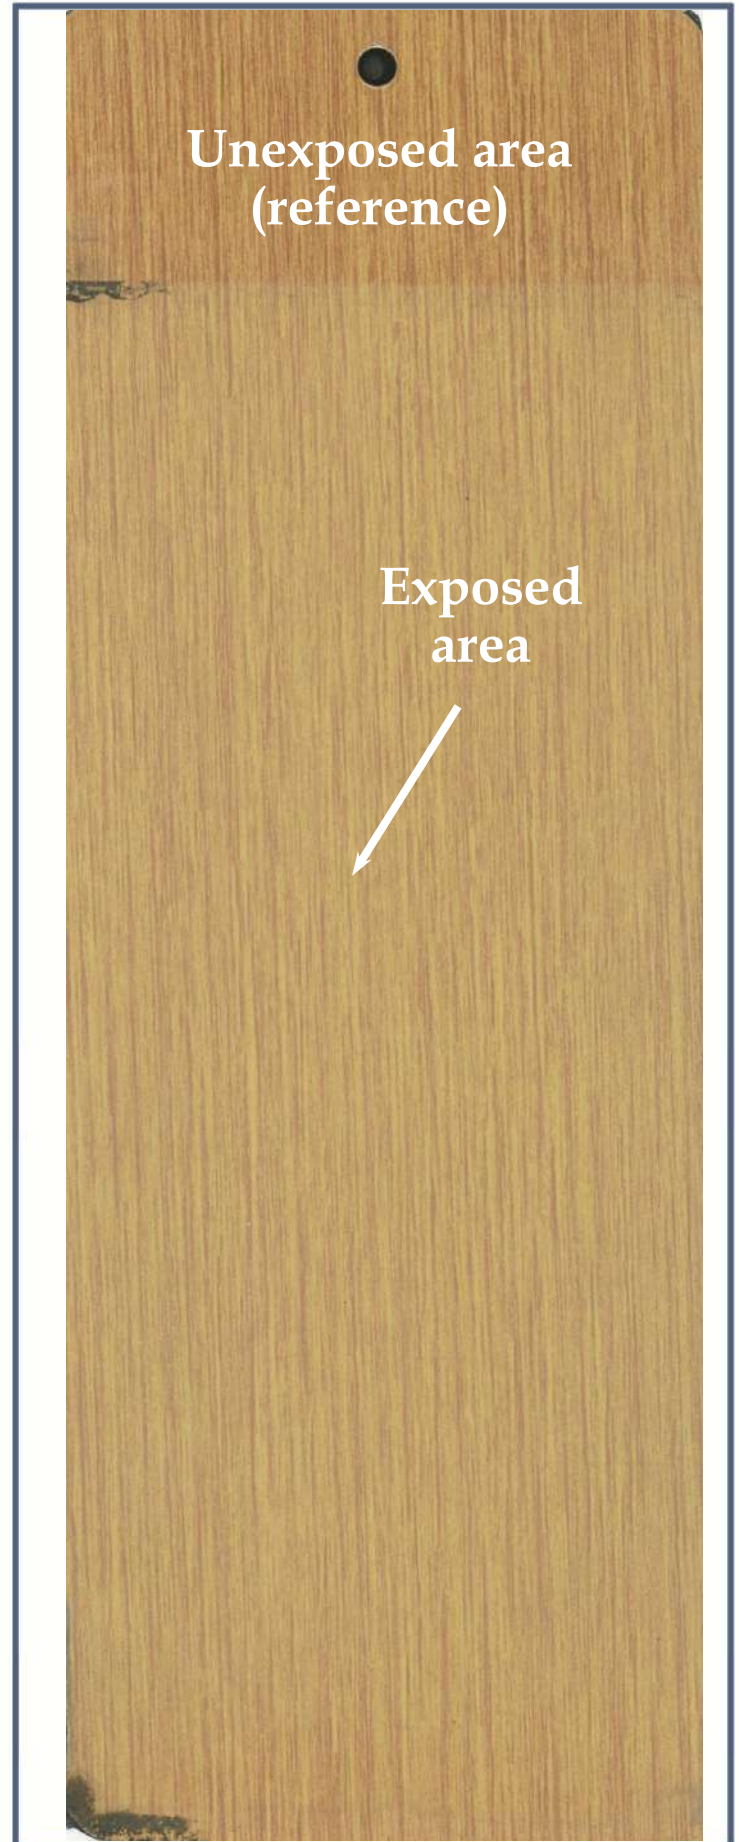





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47465  
POWDER COATING: 17C-930-A001  
HEAT TRANSFER FILM: 82102/01 L4  
colour variation ( $\Delta E$ ): **4,21**  
residual gloss: 75%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47466  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 82103/01 L4  
colour variation ( $\Delta E$ ): **4,43**  
residual gloss: **62%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47467  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 81441/01 L4  
colour variation ( $\Delta E$ ): **4,48**  
residual gloss: **91%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a excellent residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47468  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 81601/06 L4  
colour variation ( $\Delta E$ ): **4,56**  
residual gloss: **78%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47469  
POWDER COATING: 17C-930-A001  
HEAT TRANSFER FILM: 82103/01 L4  
colour variation ( $\Delta E$ ): **4,60**  
residual gloss: **81%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a good residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47470  
POWDER COATING: 17C-902-A001  
HEAT TRANSFER FILM: 81501/02 L4  
colour variation ( $\Delta E$ ): **4,80**  
residual gloss: **88%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a excellent residual gloss and high colour variation, the aspect still remains good.




Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**

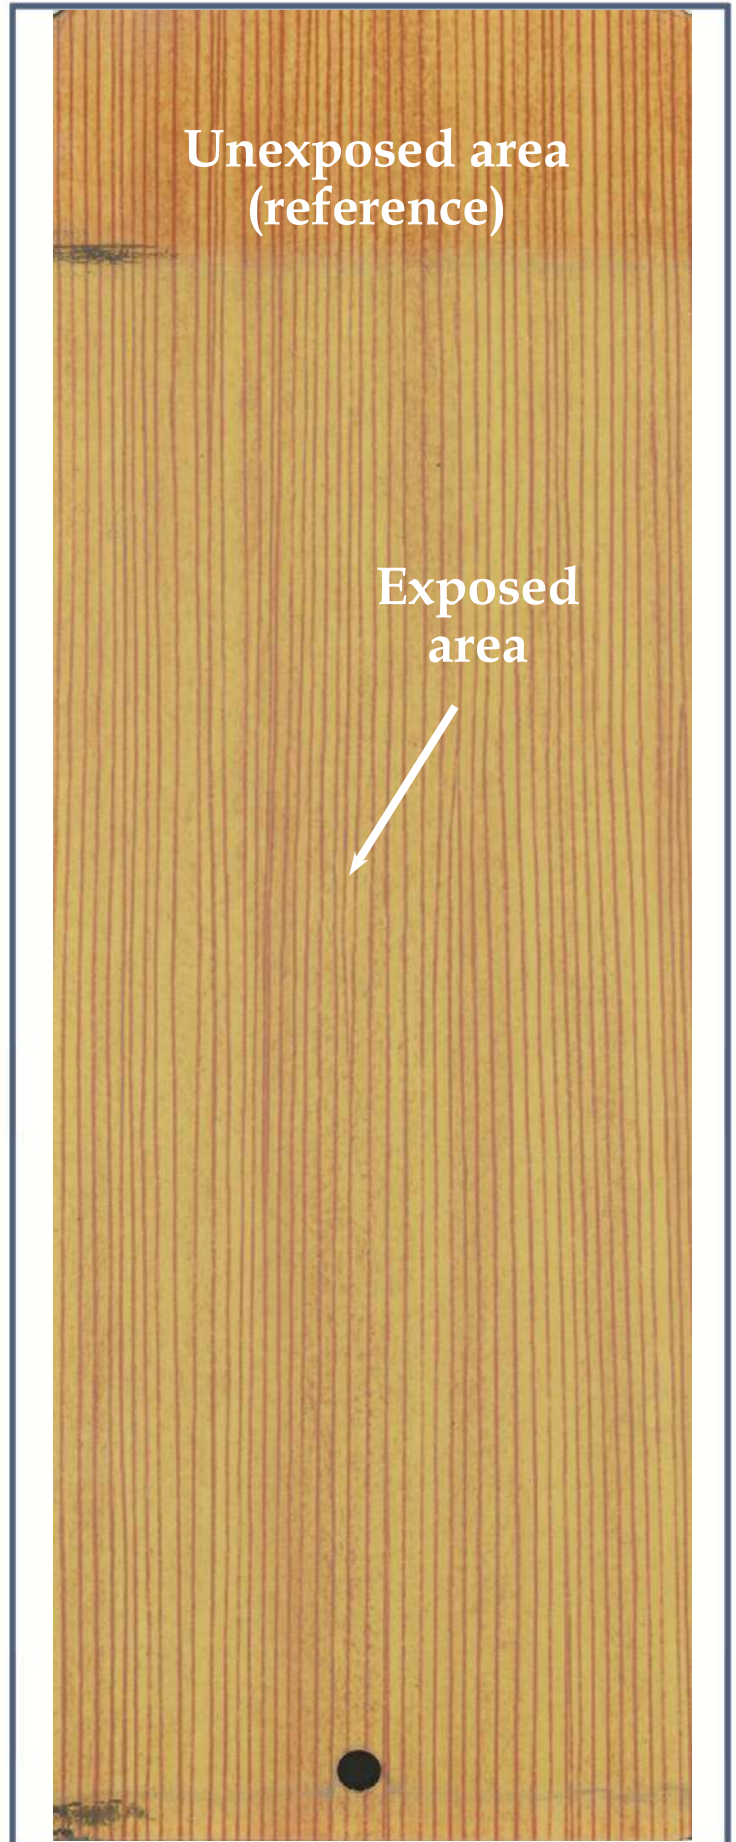



**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47471  
POWDER COATING: 17C-921-A001  
HEAT TRANSFER FILM: 81403/01 L4  
colour variation ( $\Delta E$ ): **4,88**  
residual gloss: **84%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a excellent residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**







**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47472  
POWDER COATING: 17C-906-A001  
HEAT TRANSFER FILM: 81001/09 L4  
colour variation ( $\Delta E$ ): **4,95**  
residual gloss: **68%**

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).

**Unexposed area  
(reference)**

**Exposed  
area**





**Florida  
Test**



**Total duration:  
60 months**



**EXPOSURE PERIOD:**

**FROM: 01/06/2014**

**TO: 21/07/2019**

LAB. ID NUMBER: 47473  
POWDER COATING: 17C-925-A001  
HEAT TRANSFER FILM: 82503/07 L4  
colour variation ( $\Delta E$ ): 5,06  
residual gloss: 44%

### Technical Remarks

After 5 years of exposure in Florida, the sample has a sufficient residual gloss and high colour variation, the aspect still remains good.



Test was carried on samples prepared according to technical specifications supplied by raw materials manufacturers.

The final evaluation will be based on visual inspection with the naked eye and using grey scale (ISO 105-A02).







    [www.decoral.com](http://www.decoral.com)

MRK-012-0161