


 **Florida
Test**

 **Total duration:
12 months**

 **From 15/07/2013 to 17/07/2014**

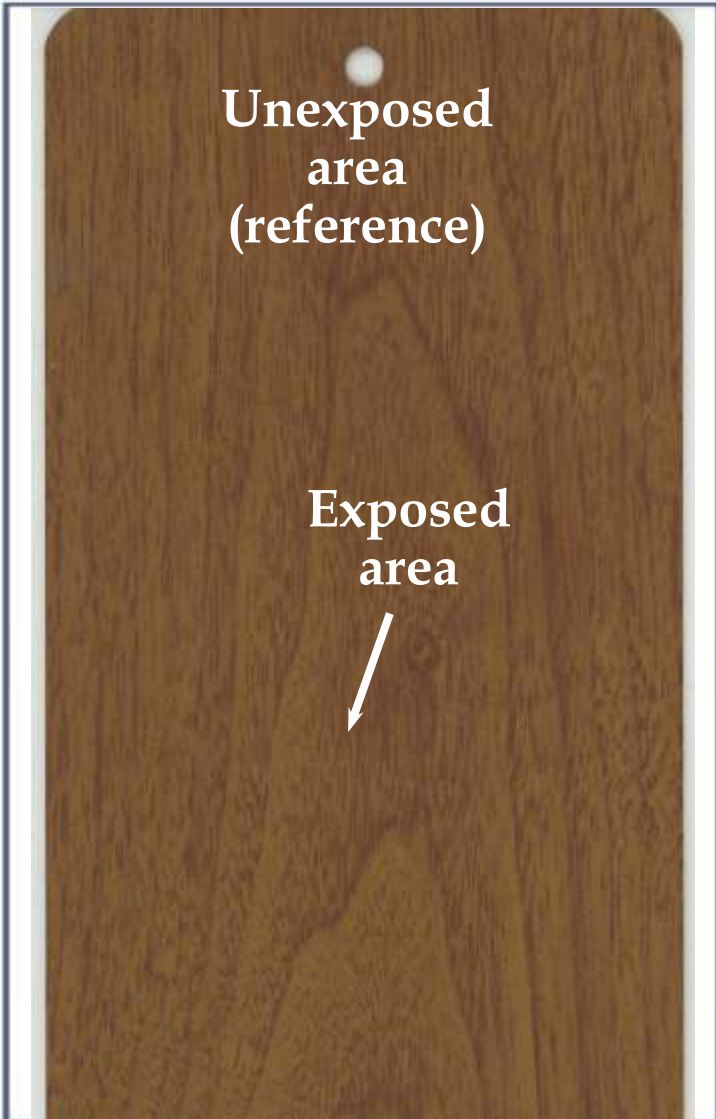

 **Florida
Test**

 **Total duration:
36 months**

 **From 15/07/2013 to 15/07/2016**



LAB. ID NUMBER: 30846
POWDER COATING: DS-0721S
HEAT TRANSFER FILM: 82505/02 L4
Colour variation (ΔE): **1,10**
residual gloss: **96%**

Approved
combination:


LAB. ID NUMBER: 31203
POWDER COATING: DS-0721S
HEAT TRANSFER FILM: 82505/02 L4
Colour variation (ΔE): **2,76**
residual gloss: **63%**

QUALICOAT REQUIREMENTS
The residual value shall be at least 75% of the original gloss.
The ΔE values not greater than 65% of the limits in the table
(see Appendix A7 of Qualicoat Specifications).

QUALICOAT REQUIREMENTS
The residual value shall be at least 50% of the original gloss.
The ΔE values within the limits prescribed in the annexed
table (see Appendix A7 of Qualicoat Specifications).